

# Low-Loss Waveguides Fabricated by Femtosecond Chirped-Pulse Oscillator

Mykhaylo Dubov, Vladimir Mezentsev, and Ian Bennion

Photonics Research Group, Aston University

12 September 2010



## Outline

Principle of femtosecond microfabrication

Historic prospective

Motivation for the present work

Fs inscription of waveguides

Waveguide characterisation


Bending losses

Conclusions



# Principle of femtosecond (fs) microfabrication

femtosecond microfabrication for dummies

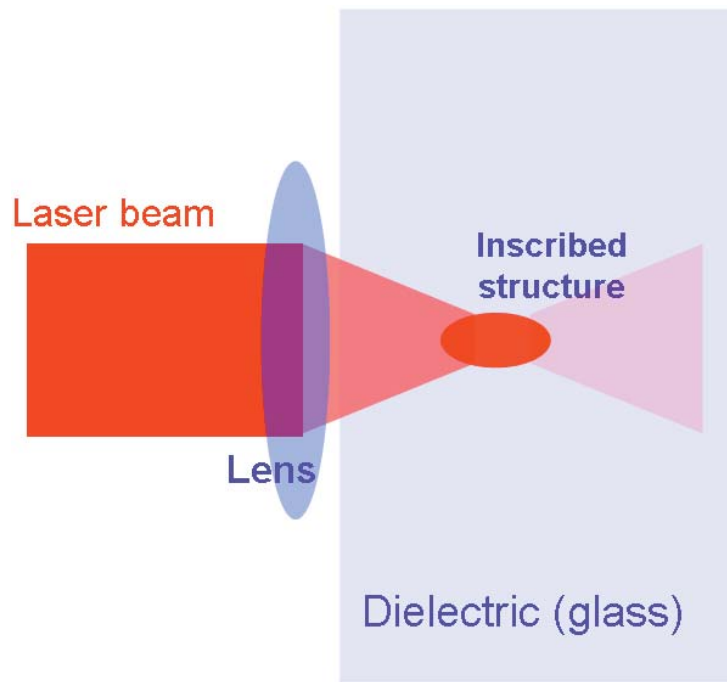


Laser pulse enters left to right




# Femtosecond micro-fabrication/machining

Experimental implementation

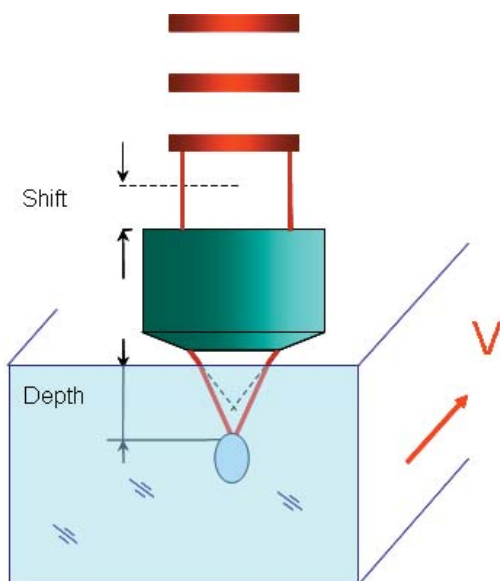

Schematic of fs inscription

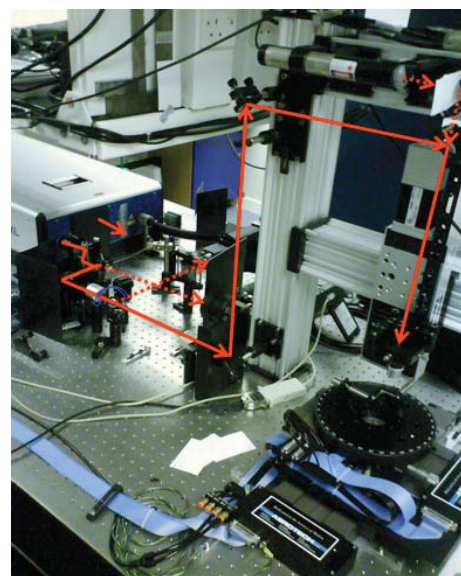

Experimental setup



## Writing waveguides in glass with a femtosecond laser

K. M. Davis, K. Miura, N. Sugimoto, and K. Hirao

Hirao Active Glass Project, Exploratory Research for Advanced Technology, Research Development Corporation of Japan, 15 Mori Moto-Cho, Shimogamo, Sakyo-Ku, Kyoto G06, Japan

Received May 6, 1996

With the goal of being able to create optical devices for the telecommunications industry, we investigated the effects of 810-nm, femtosecond laser radiation on various glasses. By focusing the laser beam through a microscope objective, we successfully wrote transparent, but visible, round-elliptical damage lines inside high-silica, borate, soda lime silicate, and fluorozirconate (ZBLAN) bulk glasses. Microellipsometer measurements of the damaged region in the pure and Ge-doped silica glasses showed a 0.01–0.035 refractive-index increase, depending on the radiation dose. The formation of several defects, including Si  $E'$  or Ge  $E'$  centers, nonbridging oxygen hole centers, and peroxy radicals, was also detected. These results suggest that multiphoton interactions occur in the glasses and that it may be possible to write three-dimensional optical circuits in bulk glasses with such a focused laser beam technique. © 1996 Optical Society of America

Since the 1970's, many investigations of the effects of UV radiation damage in high-silica glasses (especially Ge-doped silica glass) have been performed with the objective of producing optical devices (e.g., Bragg gratings) in fibers and thin films.<sup>1</sup> In contrast, laser

square-wave pulse, a uniform beam intensity, and a diameter of the laser focal point that is equal to the thickness of the observed damage lines ( $\sim 6 \mu\text{m}$ ), we found that the samples experienced 12,000 pulses/spot, and each spot was subjected to a dose of

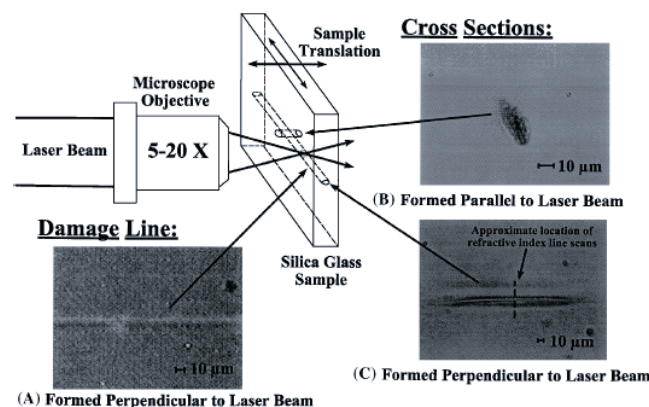


Fig. 1. Laser damage process with images of (A) a laser damage line, (B) the cross section of a line written by translation of the sample parallel to the incident laser beam, and (C) the cross section of a line written by translation of the sample perpendicular to the incident laser beam by a 5 $\times$  microscope objective. The dashed line in (C) represents the path traversed during the microellipsometer measurements.





Fig. 1. (a) Schematic of the symmetric three-waveguide directional coupler. Waveguides are initially separated by  $50 \mu\text{m}$  and by  $5 \mu\text{m}$  in interaction region  $L$ . (b) Inverse gray-scale CCD image of the waveguide outputs shows a 43:28:29 power-splitting ratio between the guides.

Microfabrication of 3D couplers. Kowalevitz et al, 2005

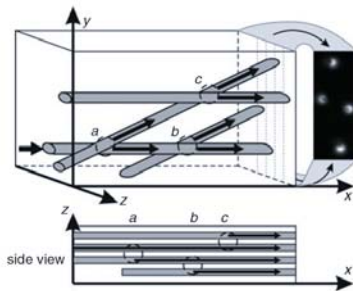


Fig. 3 Schematic of  $1 \times 4$  splitter (top and side view) with experimental near-field of output face at  $1550 \text{ nm}$

3D splitter. Osellame et al, 2005

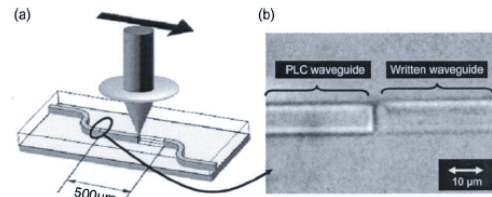


Fig. 5. (a) Schematic diagram of the waveguide connection in this experiment. (b) Image at the junction point of waveguide connection.

Lightwave Circuits. Nasu et al, 2005

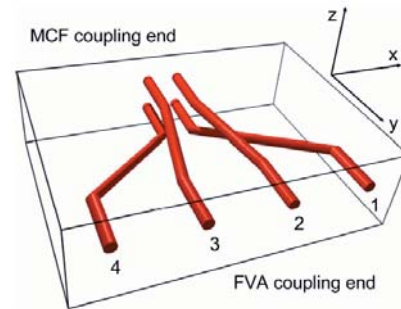


Fig. 1. Graphical representation of the fabricated fan-out device.

Fan out coupler. Thomson et al, 2007

## Motivation for the present work


- ▶ Find key parameters to achieve well performing curved waveguides in bulk materials
- ▶ Produce reliable optimised 2D/2.5D/3D structures ready for applications in integrated optics
- ▶ Demonstrate Bragg gratings embedded into waveguides in a single process of waveguide inscription.

# Choice of a chisel

Parameter	1 kHz, 800 mJ 110 fs	11 MHz, 100 nJ 45-55 fs	Enh.
Efficiency (Utilization) of Laser Energy	80-800 nJ ( $10^{-4}$ )	20-60 nJ (0.2-0.6)	$> 10^3$
Index Contrast, $\Delta n$	$> 10^{-3}$	$> 10^{-2}$	10
Translation speed, mm/s	0.01-0.1	10-100	$> 10^3$
WG diameter, mm	$< 2$	$< 20$	10

# Waveguide inscription

Shown: microphotographs of the waveguide cross-sections for translation speeds 20 to 60 mm/s increasing left to right

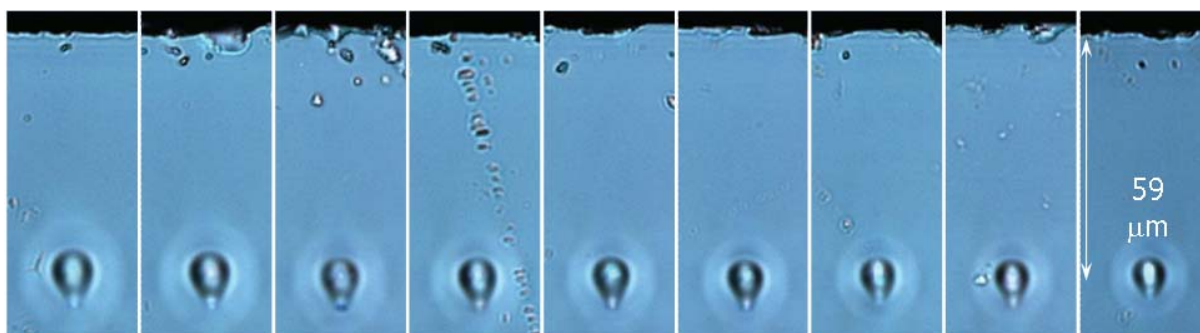

All waveguides shown above were inscribed with pulse energy of 30.7 nJ. Focal point was shifted inwards by about  $45 \mu\text{m}$  (actual depth is about  $59 \mu\text{m}$ ).

# Waveguide inscription


## Optimisation parameter space

**Optimisation Target:** lowest possible total losses of waveguide


Pulse Energy, nJ	x5	17, 19.2, ..., 31
Translation speed: mm/s	x9	20, 25, ..., 55, 60
Inscription depth, mm	x3	68, 83 and 100
Polarizations:	x2(3)	X – $\perp$ and Y – $\parallel$ to scan direction)
Translation direction	x2	Forward and Backward

Total: 540 tracks

## Morphology of smooth well performing waveguides

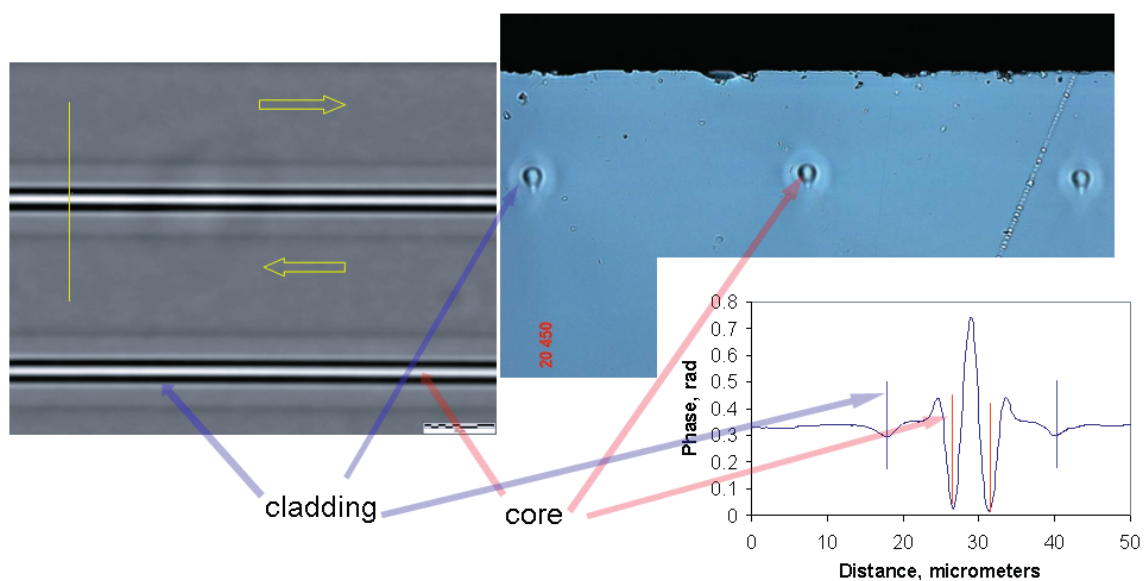


# Waveguide diameters

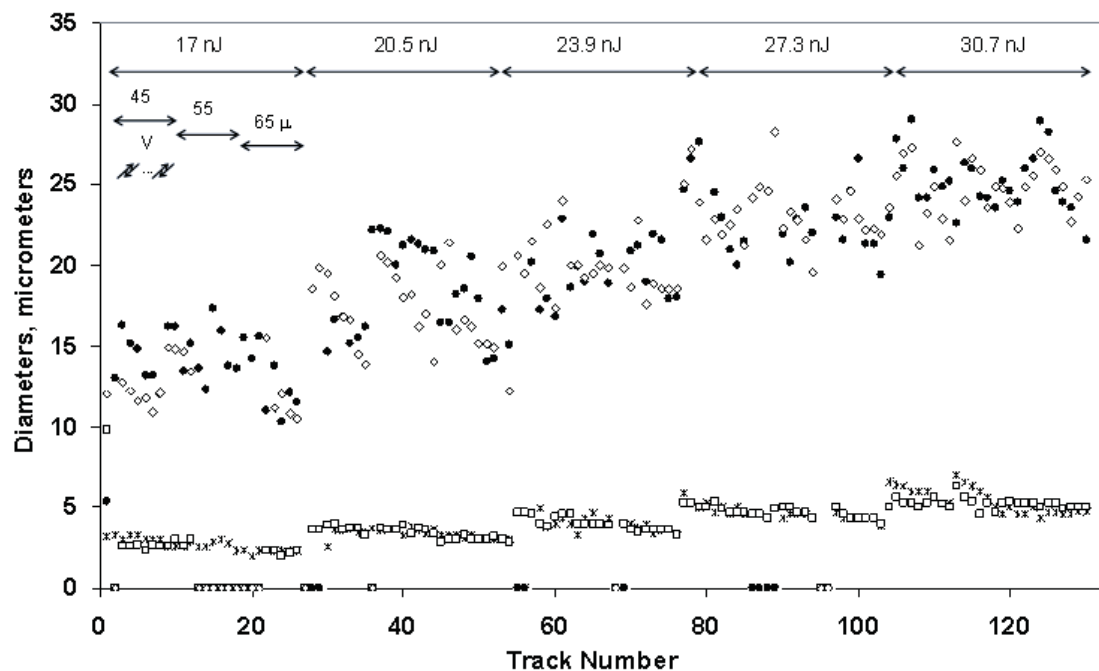


Core and cladding diameters for X ( $\diamond$  – cladding,  $\square$  – core) and Y-polarizations ( $\bullet$  – cladding,  $*$  – core).

# V-parameter for gradient index waveguides

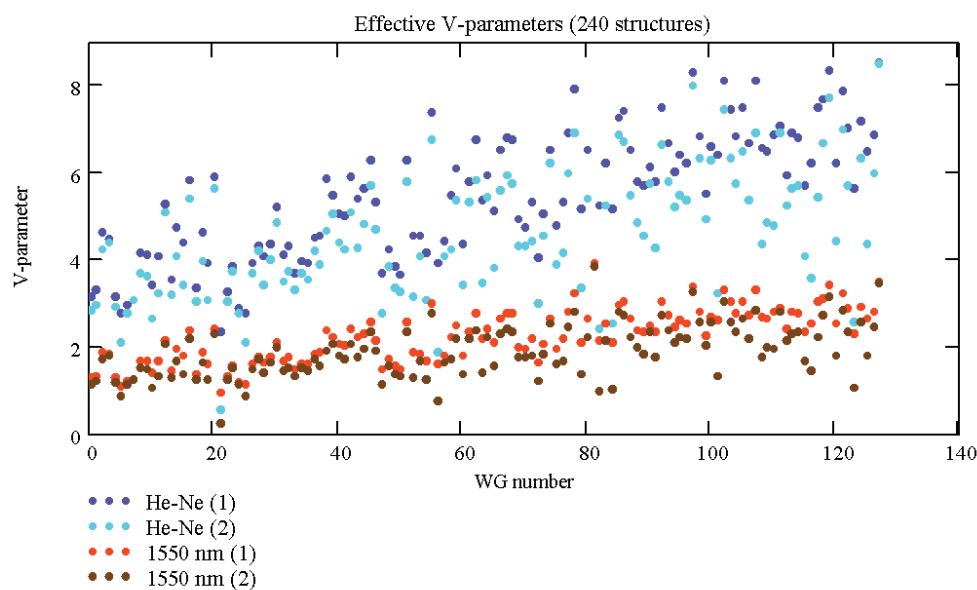


$$V = \frac{2\pi}{\lambda} \sqrt{\int_0^{\infty} (n^2(r) - n_b^2) 2r dr}$$

# A rig for waveguide characterisation

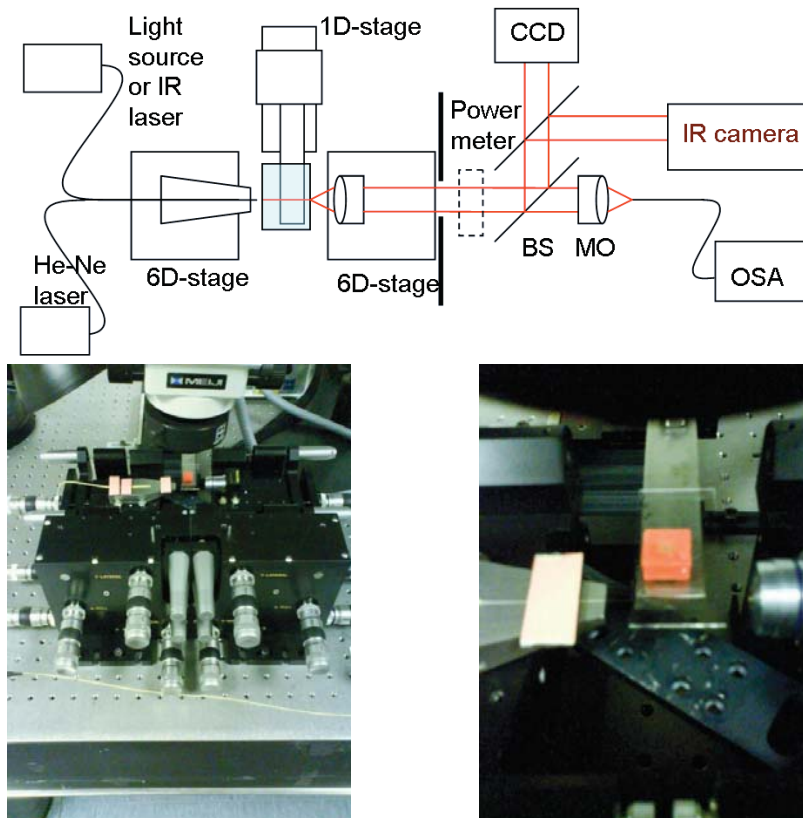

## Waveguide losses


### Treasure map

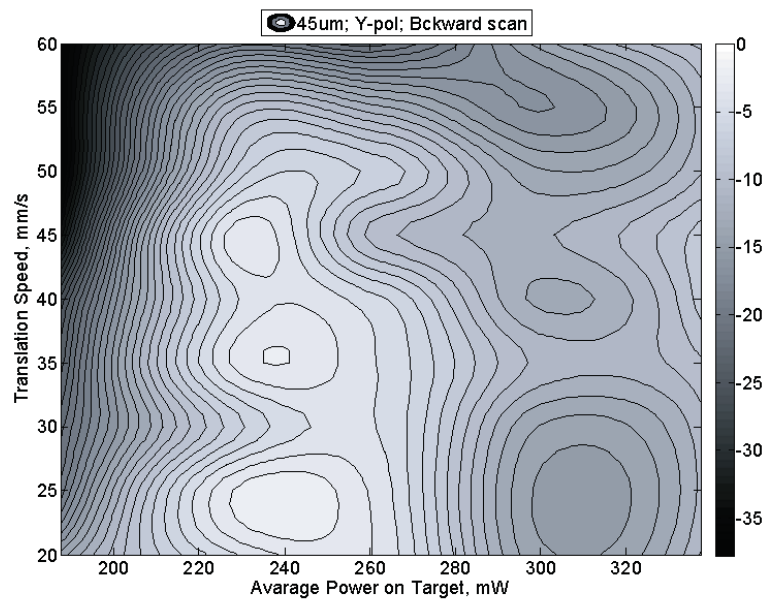

Optimal regime is an island in energy – translation speed plane.  
Propagation losses of optimal waveguides are found to be about  
**0.1 dB/cm @633 nm** and **0.5 dB/cm @1550 nm**




# Bending losses. Tracks

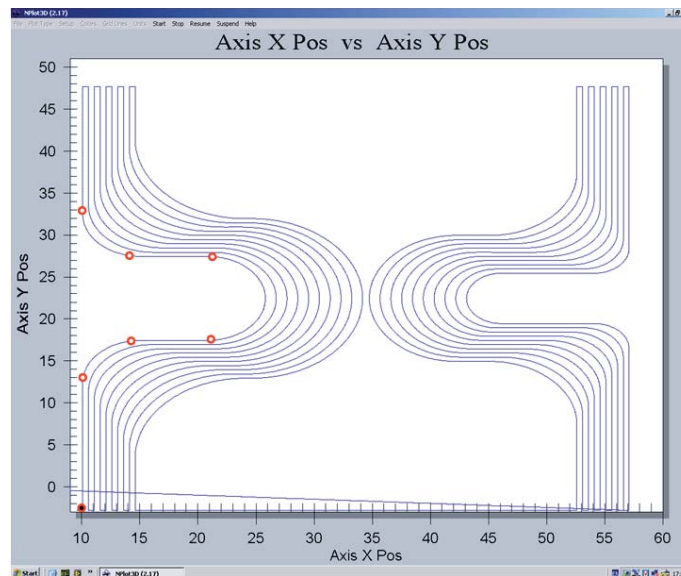



Optimal inscription regimes were exploited to manufacture **curved** tracks. All the tracks are designed to have the same length and comprise straight stretches and 4 arcs with different directions and curvatures

# Bending losses. Measurements

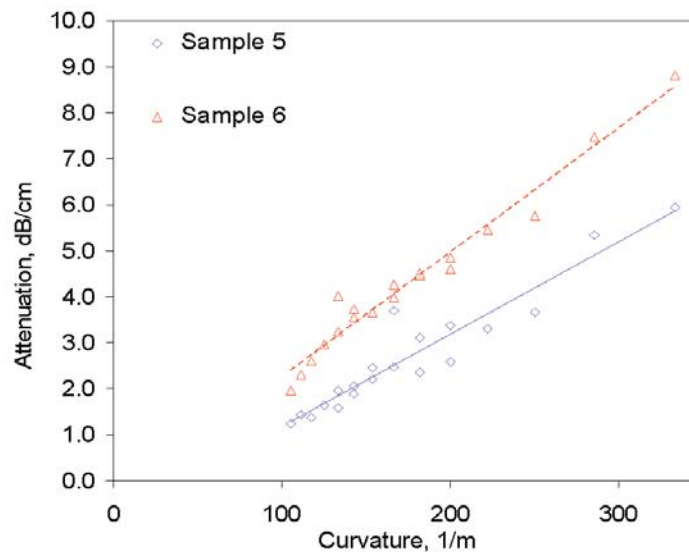

Bending losses of optimal curved tracks compare to those of fibres and are now suitable for applications in integral optics.

# Shallow and multiscan waveguides

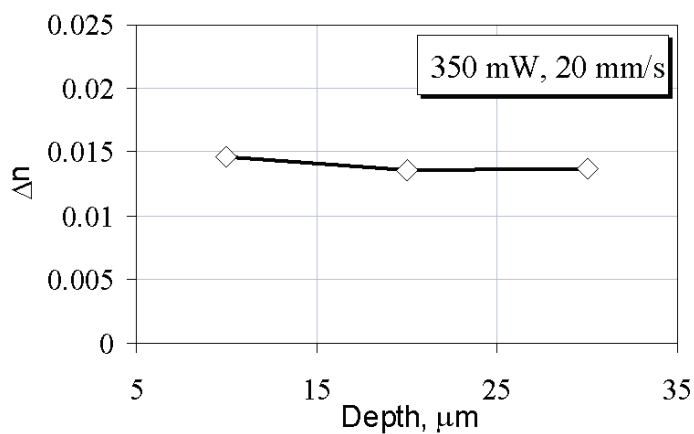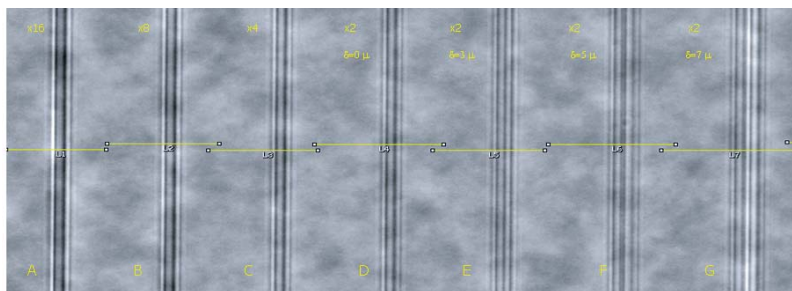

Ref. index vs depth


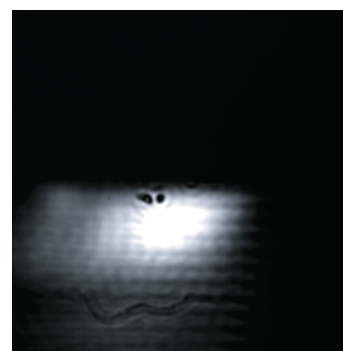


Image of near field mode

# FBG structure embedded in fs inscribed waveguide

Work in progress.

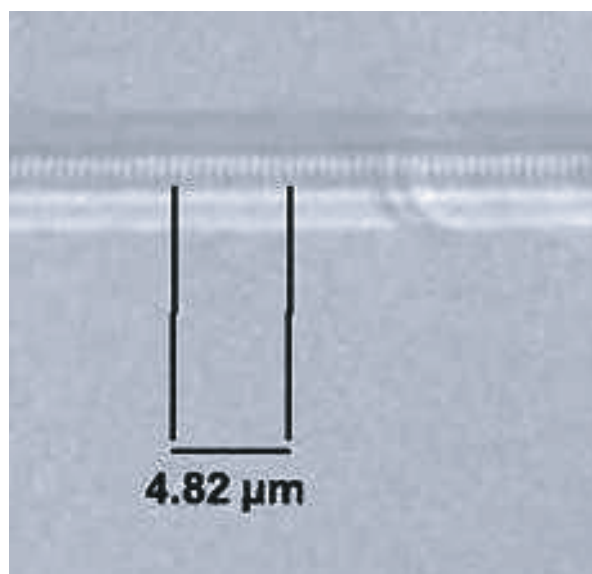

Pulse power of the beam is modulated to induce a visually perfect periodic structure.

- ▶ Operation regimes for microfabrication of waveguides suitable for application optics found.
- ▶ Curvilinear waveguides with acceptable bending losses are demonstrated.
- ▶ FBG structure embedded in the waveguide fabricated in a single process with fabrication of the waveguide.