

Passively harmonic mode-locked Erbium-doped fiber laser at a 580 MHz repetition rate based on carbon nanotubes film

Qianqian Huang(黄千千)¹, Tianxing Wang(王天行)¹, Chuanhang Zou(邹传杭)¹, Mohammed AlAraini^{2,3,4}, Aleksey Rozhin^{2,3}, and Chengbo Mou(牟成博)*¹

¹Key Laboratory of Specialty Fiber Optics and Optical Access Networks, Shanghai University, Shanghai 200072, China

²Aston Institute of Photonic Technologies (AIPt), Aston University, Birmingham, B4 7ET, United Kingdom

³Nanoscience Research Group, Aston University, Birmingham, B4 7ET, United Kingdom

⁴Al Musanna College of Technology, Muladdah, Al Musanna, P.O.Box 191, P.C.314, Sultanate of Oman

*Corresponding author: mouc1@shu.edu.cn

Received Month X, XXXX; accepted Month X, XXXX; posted online Month X, XXXX

We have proposed and demonstrated a passively harmonic mode-locked Erbium-doped fiber laser (EDFL) using carbon nanotubes polyvinyl alcohol (CNTs-PVA) film. The laser allows generation of the pulses with a repetition rate of 580 MHz, which corresponds to the 22nd harmonics of 26.3 MHz fundamental repetition rate under 323 mW pump power. A particularly noteworthy feature of the pulses is super-mode suppression ratio (SMSR), which is over 40 dB indicating a stable operation.

OCIS Codes: 140.3500, 160.4236, 320.7160.

doi:10.3788/COLXXXXX.XXXXXX.

In recent years, high repetition rate fiber laser was intensively explored which is able to pave a promising way for the applications of optical frequency metrology^[1], optical communication^[2] as well as high speed optical sampling^[3]. Ordinarily, the methods of realizing high repetition pulses focus on three aspects. An impactful approach is actively mode locking which is in a position to scale up repetition rate to a few tens of gigahertz easily while extra modulators incorporated in laser will add level of complexity^[4, 5]. Additionally, an alternative mean is to employ a short cavity. Unfortunately, the cavity length, to a great extent, is restrained by the physical size of fiber devices and limited pump power^[6-8]. Furthermore, harmonic mode-locking (HML) can be adopted to sidestep the drawback of the limitation of fiber length and achieve high repetition rate simultaneously, where multiple solitons due to high pump power^[9, 10] organize themselves and exhibit equal spacing between adjacent pulses under a specific condition^[11, 12].

Thus far, passive mode-locking (PML) fiber laser with some unique features of compact size, superior heat dissipation performance and fairly easy maintenance has motivated much interest. There are various approaches to obtain mode locked pulses such as nonlinear polarization rotation (NPR)^[13,14], nonlinear optical loop mirror (NOLM)^[15], semiconductor saturable absorber mirror (SESEAM)^[16], and the carbon based saturable absorbers (SAs) including nanoscale graphite^[17], charcoal^[18] and CNTs^[19-21]. Especially, most of them also have been demonstrated to achieve HML. In particular, CNTs are intensively applied SA which process favorable properties of fast recovery time, wideband wavelength range as well

as being insensitive to environmental perturbation^[22]. Moreover, in order to improve damage threshold and emit higher energy, a CNT SA of the evanescent-wave interaction type is proposed which is formed by deposition on a D-shaped fiber^[23], a fiber taper^[24] or a microfiber^[25]. Jun *et al.* firstly obtained 943 MHz pulse train at 34th harmonics with excellent noise performance under 195 mW pump power^[26]. Furthermore, through engineering the dispersion of the cavity, 4.9 GHz pulses, corresponding to 128th HML was finally realized under 395 mW pump power with 40 dB SMSR^[27]. However, the structure is considerably conditional on the special fiber devices which will bring additional complexity of the system^[28]. Another credible SA type is CNTs film sandwiched between two fiber connector ferrules exhibiting virtues of simple construction, mature manufacturing, easy implementation and high flexibility^[29-31]. Nevertheless, the CNTs film is rarely exploited to achieve a relatively repetition rate pulse train. Up to now, the highest repetition rate of 328 MHz corresponding to 23rd harmonics with larger than 30 dB SMSR has been examined by passively harmonically mode-locked fiber laser using CNTs film^[32].

In this work, we experimentally demonstrate passively HML of an EDFL using CNTs-PVA film. After adjusting the intra-cavity birefringence slightly, the laser is in a position to deliver pulses train with 580 MHz repetition rate corresponding to the 22nd harmonics of 26.3 MHz fundamental repetition rate under 323 mW pump power. To the best of our knowledge, this is the highest repetition rate achieved by using CNTs film as SA. Especially, the radio frequency (RF) spectrum indicating 40.6 dB SMSR

which is significantly preferred to prior HML laser reported in Ref. [24]. Also, other systematic performances of the train are depicted. The demonstrated laser system attests that it is potential to generate pulses with high repetition rate just using CNTs film by means of HML.

The experimental configuration of proposed CNTs-PVA film based fiber laser is illustrated in Fig.1. 98.2 cm Erbium-doped fiber (EDF Er110-4/125 from Liekki) functions as gain medium whose signal gain is 110 dB/m at 1530 nm with a normal dispersion of $+12 \text{ ps}^2/\text{km}$ at 1550 nm. A 980 nm benchtop laser (OV LINK, Wuhan, China) with the maximum pump power of 710 mW provides pump light which is launched into cavity resonator through a wavelength-division multiplexer (WDM) coupler. 55.8 cm OFS 980 which is the pigtail of the WDM coupler offers group velocity dispersion (GVD) of $+4.5 \text{ ps}^2/\text{km}$. 20% pulse energy is tapped out with an 80:20 optical coupler (OC). In order to transmit light unidirectionally, one polarization independent isolator (ISO) is employed while a polarization controller (PC) is placed beside ISO to control the cavity polarization. The CNTs-PVA film is incorporated into the resonator by sandwiching between two fiber connectors directly served as SA. The cavity length is 7.91 m which corresponds to 26.3 MHz fundamental repetition rate including 153.3 cm HI 1060 with a GVD coefficient of $-6.6 \text{ ps}^2/\text{km}$ and 470.6 cm standard single mode fiber (SMF) with a GVD coefficient of $-21.67 \text{ ps}^2/\text{km}$. Therefore, the total dispersion is -0.104 ps^2 which leads to laser operation in the soliton regime. The characteristics of the output beam is recorded by an optical spectrum analyzer (OSA, Yokogawa AQ6370C), a 1 GHz oscilloscope (OSC, Tektronix MSO4104) with a 12.5 GHz photo-detector (PD, Newport 818-BB-51F), a RF spectrum analyzer (SIGLENT, SSA 3032X) together with a commercial autocorrelator (FEMTOCHROME, FR-103WS).

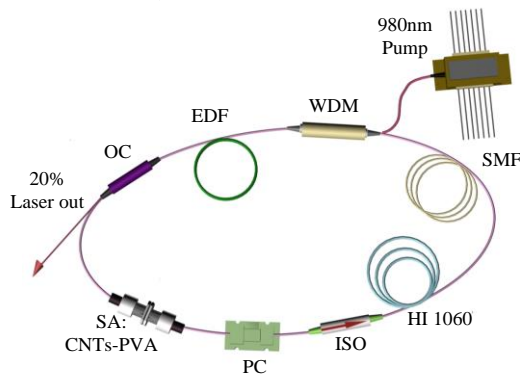


Fig. 1. Schematic configuration of a passively HML fiber laser with CNTs-PVA film

The production process of CNTs-PVA film is similar to Ref. [25]. The linear optical absorption spectrum of the CNTs-PVA film is depicted in Fig. 2(a) which gives a broad absorption band and the absorbance is nearly 0.2 at 1550 nm. Fig. 2(b) is the measured Raman spectrum with

excitation wavelength of 532 nm. Because the radial breathing mode (RBM) is in relation to the diameter of CNTs^[33], we can calculate a mean nanotube diameter of 0.88 nm according to $250 \text{ cm}^{-1}\text{RBM}$. Moreover, the existence of RBM and G mode (1588 cm^{-1}) suggests the CNTs are single walled. We have also found that D mode is hard to detect declaring high quality of the CNTs sample. Fig. 2(c) shows the measured nonlinear transmission and from which the modulation depth can be estimated about 6.2% which gives a full proof that the CNTs-PVA film have the capability to be served as an ideal mode locker.

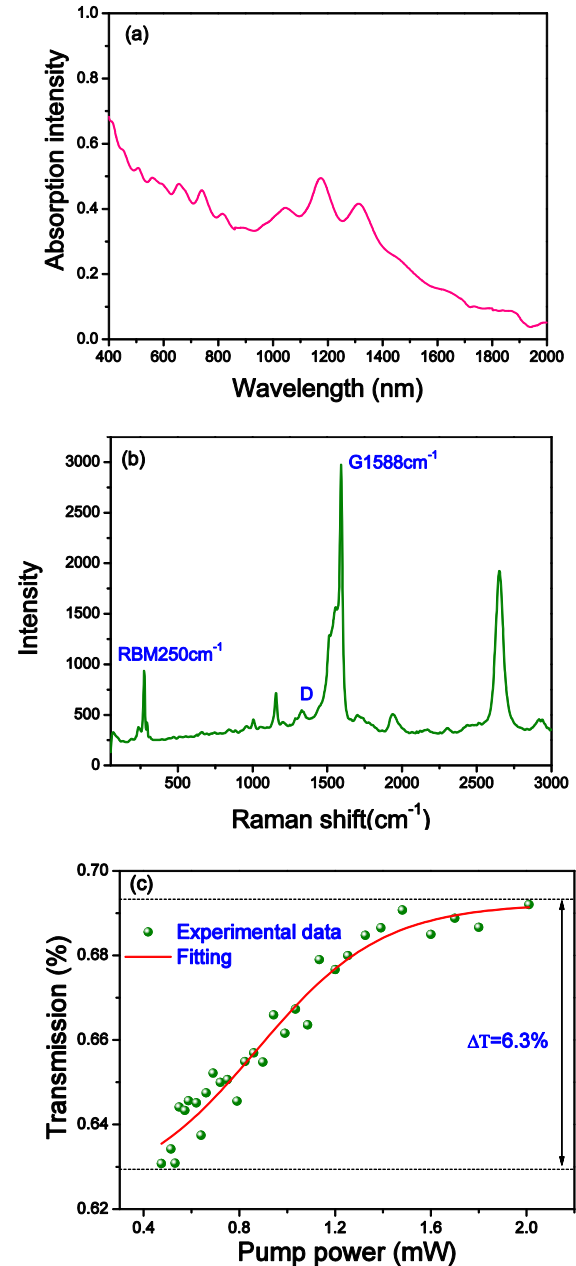


Fig. 2. (a) Absorption spectrum of the CNTs-PVA film. (b) Measured Raman spectrum of the CNTs-PVA film under

pump laser of 532 nm. (c) The measured nonlinear transmission of CNTs-PVA film.

Mode locked operation occurred when pump power reaches 88 mW with proper adjustment of PC. Fig. 3 presents some characteristics of pulses under 95.6 mW pump power. The RF spectrum illustrated in Fig. 3(a) shows the laser works in a single pulse state with 26.3 MHz fundamental repetition rate which quite agrees with 7.91 m cavity length while the inset of Fig. 3(a) shows that 3 dB bandwidth of the pulses is 5.8 nm with 1563.48 nm center wavelength. Also, the existence of Kelly sideband confirms that the laser operates in the soliton regime. Fig. 3(b) is the corresponding oscilloscope image and from which it is apparent that the envelope of the mode-locked pulse train consists of a tiny peak fluctuation with $dI/I \sim 4\text{-}5\%$ suggesting a slightly unstable state. The measured output power is 0.328 mW.

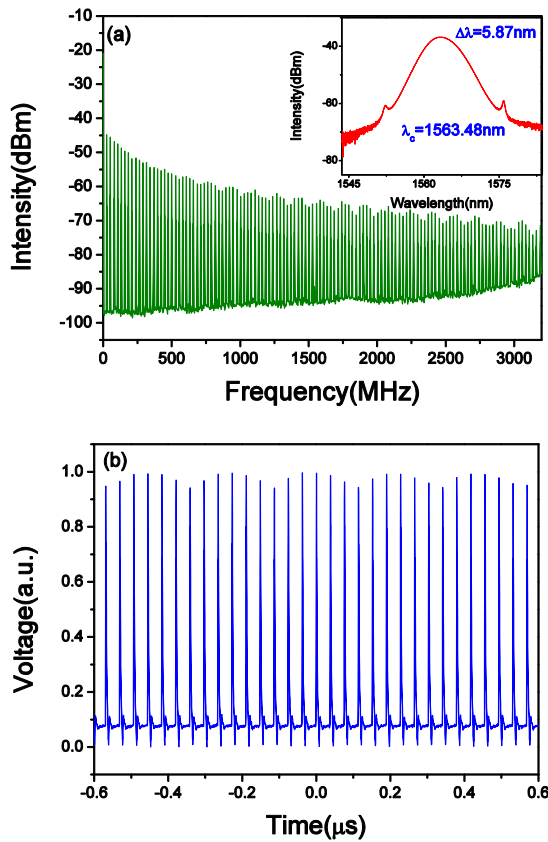


Fig. 3. The characteristics of pulses with 26.3 MHz fundamental repetition rate under 95.6 mW pump power: (a) RF spectrum with a 3.2 GHz span and 10 kHz resolution bandwidth. Inset is the corresponding optical spectrum. (b) Oscilloscope trace.

$2^{\text{nd}} \sim 22^{\text{nd}}$ order HML can be observed in the wake of increasing pump power continually. When 323 mW pump power is applied, the 22th HML pulses at 580 MHz repetition rate appear with 4.9 mW output power. The

pulses train is shown in Fig. 4 from which we can see that the interval between adjacent pulses is well-distributed and equally spaced. It is measured to be 1.72 ns indicating 580 MHz repetition rate.

As universally known, the RF spectrum plays a great role in evaluating the stability of the laser operation depicted in Fig. 5. The maximum peak in Fig. 5 located in 580 MHz further verifies the repetition rate of the pulses. The SMSR at the level of 40.6 dB is prevailed over the previous report [32] and the signal-to-noise ratio (SNR) is 48.2 dB. Both of them manifest that the laser possesses good stability. Fig. 6. is the corresponding optical spectrum centered at 1560.13 nm with 2.55 nm bandwidth. The autocorrelation trace as illustrated in Fig. 7 implies that the pulse duration is 2.17 ps when fitted by a sech^2 pulse shape. Thus, the time bandwidth product (TBP) is reckoned to be 0.682 indicating slight pulse chirp. Furthermore, shorter pulsedwidth and more stable pulses may be obtained if we optimize CNT dopant concentration in the PVA film carefully or adjust the pump power properly^[30,34].

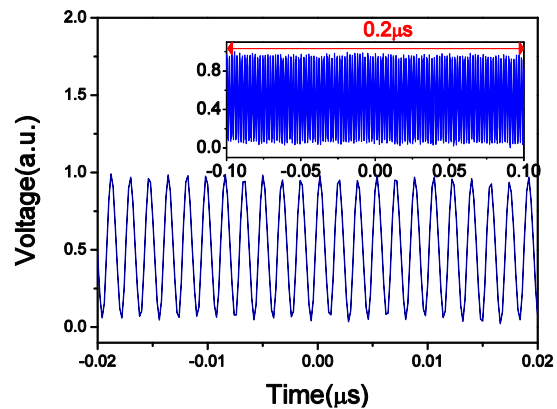


Fig. 4. Observed pulses train at 580 MHz repetition rate. Inset presents pulses train within the range of 0.2 μs.

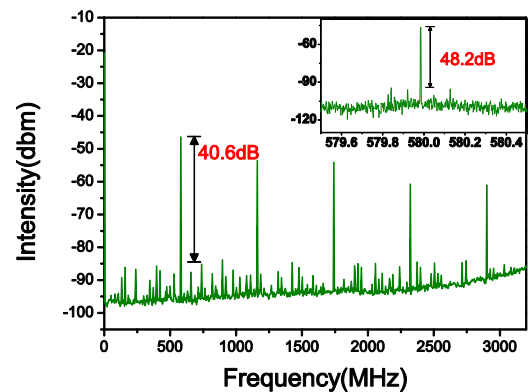


Fig. 5. RF spectrum over 3.2 GHz span of the emitted light from the fiber laser. The RF peak of the insert map is 580 MHz.

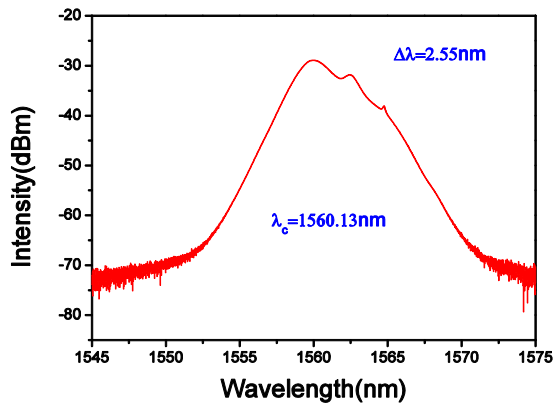


Fig. 6. Optical spectrum of the pulses.

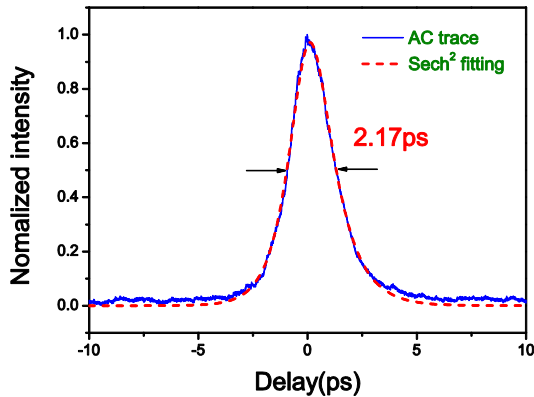


Fig. 7. Autocorrelation trace of the pulses.

The relation of harmonic order versus pump power is plotted in Fig. 8. As we can see, the harmonic order varies from 2 to 22 when pump power increases from 95.6 mW to 323 mW. It is apparent that the trend of the variation of harmonic order is nearly linear. In our experiment, when the pump power raising further, Q-switching will arise instead of mode locking operation. Considering the soliton area theorem^[35], higher repetition rate pulses are expected to achieve though optimizing laser average dispersion appropriately to get the less soliton energy^[11,21].

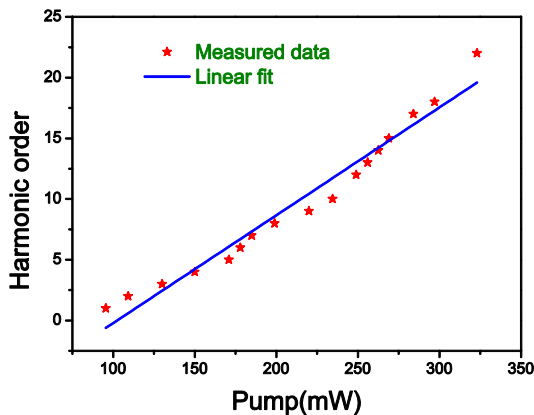


Fig. 8. Harmonic order as a function of pump power.

In conclusion, we have demonstrated passively HML of an EDFL using CNTs film as SA. Though increasing pump power and manipulating the polarization controller, 580 MHz repetition rate pulses corresponding to the 22nd harmonics of 26.3 MHz fundamental repetition rate can be realized, which, to the best of our knowledge, are the highest repetition rate pulses generated from an EDFL based on CNTs film. Particularly, the stability of the pulses is proved by 40.6 dB SMSR. And the laser can work for several hours at a stable operation. Furthermore, our experiment results inspire us to reveal that CNTs polymer composite film is able to function as a SA applied in fiber laser to obtain high repetition rate pulses via HML.

The authors would like to gratitude to the National Natural Science Foundation of China (NSFC) (61605107), Young Eastern Scholar Program at Shanghai Institutions of Higher Learning (QD2015027) and "Young 1000 Talent Plan" Program of China for their great support to our investigation. The authors also would like to acknowledge support from the Ministry of Higher Education, Sultanate of Oman; Marie Sklodowask-Curie IEF project(H2020-MSCA-IF-2014_ST, Proposal#:656984); Marie-Curie Inter-national Research Staff Exchange Scheme "TelaSens" project, Research Executive Agency Grant No. 269271, Programme: FP7-PEOPLE-2010-IRSES.

References

1. R. J. Jones and J.-C. Diels, "Stabilization of femtosecond lasers for optical frequency metrology and direct optical to radio frequency synthesis," *Physical review letters* 86, 3288 (2001).
2. H. A. Haus and W. S. Wong, "Solitons in optical communications," *Reviews of modern physics* 68, 423 (1996).
3. J. B. Schlager, P. D. Hale, and D. L. Franzen, "High - sensitivity optical sampling using an erbium - doped fiber laser strobe," *Microwave and Optical Technology Letters* 6, 835 (1993).
4. W.-W. Hsiang, C.-Y. Lin, M.-F. Tien, and Y. Lai, "Direct generation of a 10 GHz 816 fs pulse train from an erbium-fiber soliton laser with asynchronous phase modulation," *Optics letters* 30, 2493 (2005).
5. R. Wang, Y. Dai, F. Yin, K. Xu, L. Yan, J. Li, and J. Lin, "High-repetition-rate, stretch-lens-based actively-mode-locked femtosecond fiber laser," *Optics express* 21, 20923 (2013).
6. H. Qi, J. Zhang, G. Zhou, A. Wang, and Z. Zhang, "325 MHz and near transform-limited pulse output directly from an Er: fiber ring laser," *Chinese Optics Letters* 11, 061402 (2013).
7. L. Zhao, C. Lu, H. Tam, P. Wai, and D. Tang, "High fundamental repetition rate fiber lasers operated in strong normal dispersion regime," *IEEE Photonics Technology Letters* 21, 724 (2009).
8. Y. L. Qi, H. Liu, H. Cui, Y. Q. Huang, Q. Y. Ning, M. Liu, Z. C. Luo, A. P. Luo, and W. C. Xu, "Graphene-deposited microfiber photonic device for ultrahigh-repetition rate pulse generation in a fiber laser," *Optics Express* 23, 17720 (2015).

9. Y. F. Song, L. Li, H. Zhang, D. Y. Tang, and K. P. Loh, "Vector multi-soliton operation and interaction in a graphene mode-locked fiber laser," *Optics express* 21, 10010 (2013).
10. D. Tang, L.-M. Zhao, B. Zhao, and A. Liu, "Mechanism of multisoliton formation and soliton energy quantization in passively mode-locked fiber lasers," *Physical Review A* 72, 043816 (2005).
11. Z. C. Luo, M. Liu, H. Liu, X. W. Zheng, A. P. Luo, C. J. Zhao, H. Zhang, S. C. Wen, and W. C. Xu, "2 GHz passively harmonic mode-locked fiber laser by a microfiber-based topological insulator saturable absorber," *Optics Letters* 38, 5212 (2013).
12. G. Sobon, J. Sotor, and K. M. Abramski, "Passive harmonic mode-locking in Er-doped fiber laser based on graphene saturable absorber with repetition rates scalable to 2.22 GHz," *Applied Physics Letters* 100, 161109 (2012).
13. S. Tao, L. Xu, G. Chen, C. Gu, and H. Song, "Ultra-high repetition rate harmonic mode-locking generated in a dispersion and nonlinearity managed fiber laser," *Journal of Lightwave Technology* 34, 2354 (2016).
14. S. Zhou, D. G. Ouzounov, and F. W. Wise, "Passive harmonic mode-locking of a soliton Yb fiber laser at repetition rates to 1.5 GHz," *Optics letters* 31, 1041 (2006).
15. H. Sotobayashi, C. Sawaguchi, Y. Koyamada, and W. Chujo, "Ultrafast walk-off-free nonlinear optical loop mirror by a simplified configuration for 320-Gbit/s time-division multiplexing signal demultiplexing," *Optics letters* 27, 1555 (2002).
16. Y. Deng, M. Koch, F. Lu, G. W. Wicks, and W. H. Knox, "Colliding-pulse passive harmonic mode-locking in a femtosecond Yb-doped fiber laser with a semiconductor saturable absorber," *Optics express* 12, 3872 (2004).
17. G. R. Lin and Y. C. Lin, "Directly exfoliated and imprinted graphite nano-particle saturable absorber for passive mode-locking erbium-doped fiber laser," *Laser Physics Letters* 8, 880 (2011).
18. Y. H. Lin, Y. C. Chi, and G. R. Lin, "Nanoscale charcoal powder induced saturable absorption and mode-locking of a low-gain erbium-doped fiber-ring laser," *Laser Physics Letters* 10, 055105 (2013).
19. H. Li, S. Zhang, J. Du, Y. Meng, Y. Hao, and X. Li, "Passively harmonic mode-locked fiber laser with controllable repetition rate based on a carbon nanotube saturable absorber," *Optics Communications* 285, 1347 (2012).
20. C. Mou, R. Arif, A. Rozhin, and S. Turitsyn, "Passively harmonic mode locked erbium doped fiber soliton laser with carbon nanotubes based saturable absorber," *Optical Materials Express* 2, 884 (2012).
21. K.-N. Cheng, Y.-H. Lin, and G.-R. Lin, "Single-and double-walled carbon nanotube based saturable absorbers for passive mode-locking of an erbium-doped fiber laser," *Laser Physics* 23, 045105 (2013).
22. S. Kivistö, T. Hakulinen, A. Kaskela, B. Aitchison, D. P. Brown, A. G. Nasibulin, E. I. Kauppinen, A. Härkönen, and O. G. Okhotnikov, "Carbon nanotube films for ultrafast broadband technology," *Optics express* 17, 2358 (2009).
23. Y.-W. Song, S. Yamashita, and S. Maruyama, "Single-walled carbon nanotubes for high-energy optical pulse formation," *Applied Physics Letters* 92, 021115 (2008).
24. Y.-W. Song, K. Morimune, S. Y. Set, and S. Yamashita, "Polarization insensitive all-fiber mode-lockers functioned by carbon nanotubes deposited onto tapered fibers," *Applied Physics Letters* 90, 021101 (2007).
25. Z. Yu, Y. Wang, X. Zhang, X. Dong, J. Tian, and Y. Song, "A 66 fs highly stable single wall carbon nanotube mode locked fiber laser," *Laser Physics* 24, 015105 (2013).
26. C. S. Jun, J. H. Im, S. H. Yoo, S. Y. Choi, F. Rotermund, D.-I. Yeom, and B. Y. Kim, "Low noise GHz passive harmonic mode-locking of soliton fiber laser using evanescent wave interaction with carbon nanotubes," *Optics express* 19, 19775 (2011).
27. C. S. Jun, S. Y. Choi, F. Rotermund, B. Y. Kim, and D.-I. Yeom, "Toward higher-order passive harmonic mode-locking of a soliton fiber laser," *Optics letters* 37, 1862 (2012).
28. T. Wang, Z. Yan, C. Mou, K. Zhou, and L. Zhang, "Stable nanosecond passively Q-switched all-fiber erbium-doped laser with a 45° tilted fiber grating," *Applied Optics* 56, 3583 (2017).
29. C. Zou, T. Wang, Z. Yan, Q. Huang, M. AlAraini, A. Rozhin, and C. Mou, "Wavelength-tunable passively mode-locked Erbium-doped fiber laser based on carbon nanotube and a 45° tilted fiber grating," *Optics Communications* (2017).
30. K.-N. Cheng, Y.-H. Lin, S. Yamashita, and G.-R. Lin, "Harmonic order-dependent pulsewidth shortening of a passively mode-locked fiber laser with a carbon nanotube saturable absorber," *IEEE Photonics Journal* 4, 1542 (2012).
31. Y.-C. Lin, K.-N. Cheng, and G.-R. Lin, "Passively harmonic mode-locking of fiber ring laser using a carbon-nanotube embedded PVA saturable absorber," in *Opto-Electronics and Communications Conference (OECC), 2011 16th*, (2011), 788.
32. K. Jiang, S. Fu, P. Shum, and C. Lin, "A wavelength-switchable passively harmonically mode-locked fiber laser with low pumping threshold using single-walled carbon nanotubes," *IEEE Photonics Technology Letters* 22, 754 (2010).
33. D. Kahn and J. P. Lu, "Vibrational modes of carbon nanotubes and nanoropes," *Physical Review B* 60, 6535 (1999).
34. J.-C. Chiu, C.-M. Chang, B.-Z. Hsieh, S.-C. Lin, C.-Y. Yeh, G.-R. Lin, C.-K. Lee, J.-J. Lin, and W.-H. Cheng, "Pulse shortening mode-locked fiber laser by thickness and concentration product of carbon nanotube based saturable absorber," *Optics express* 19, 4036 (2011).
35. L. Nelson, D. Jones, K. Tamura, H. Haus, and E. Ippen, "Ultrashort-pulse fiber ring lasers," *Applied Physics B: Lasers and Optics* 65, 277 (1997).