

Chemical Science

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: E. Raphael, M. J. Derry, M. Hippler and S. P. Armes, *Chem. Sci.*, 2021, DOI: 10.1039/D1SC03156B.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Tuning the Properties of Hydrogen-bonded Block Copolymer Worm Gels Prepared via Polymerization-Induced Self-Assembly

Eleanor Raphael,^a Matthew J. Derry,^{*,a,b} Michael F. A. Hippler^a and Steven P. Armes^{*,a}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Polymerization-induced self-assembly (PISA) is exploited to design hydrogen-bonded poly(stearyl methacrylate)-poly(benzyl methacrylate) [PSMA-PBzMA] worm gels in *n*-dodecane. Using a carboxylic acid-based RAFT agent facilitates hydrogen bonding between neighboring worms to produce much stronger physical gels than those prepared using the analogous methyl ester-based RAFT agent. Moreover, tuning the proportion of these two types of end-groups on the PSMA chains enables the storage modulus (G') of the 20% w/w worm gel to be tuned from ~4.5 kPa up to ~114 kPa. This is achieved via two complementary routes: (i) an *in situ* approach using binary mixtures of acid- and ester-capped PSMA stabilizer chains during PISA or (ii) a post-polymerization processing strategy using a thermally-induced worm-to-sphere transition to mix acid- and ester-functionalized spheres at 110 °C that fuse to form worms on cooling to 20 °C. SAXS and rheology studies of these hydrogen-bonded worm gels provide detailed insights into their inter-worm interactions and physical behavior, respectively. In the case of the carboxylic acid-functionalized worms, SAXS provides direct evidence for additional inter-worm interactions, while rheological studies confirm both a significant reduction in critical gelation concentration (from approximately 10% w/w to 2-3% w/w) and a substantial increase in critical gelation temperature (from 41 °C to 92 °C). It is remarkable that a rather subtle change in the chemical structure results in such improvements in gel strength, gelation efficiency and gel cohesion.

Introduction

Hydrogen bonding is widely regarded as the most important example of a non-covalent interaction between molecules.¹⁻⁴ Indeed, hydrogen bonding is an essential component of the secondary structure of DNA via formation of complementary base pairs.⁵ This well-known phenomenon has been exploited in polymer science by various research groups to generate supramolecular morphologies, as well as to tune mechanical properties.⁶⁻¹⁰ For example, 2-ureido-4[1H]-pyrimidone (UPy) motifs have been used to introduce highly cooperative hydrogen bonding interactions in either aqueous or non-aqueous media.^{6, 9, 11-14} Thus, Meijer and co-workers⁹ prepared poly(ethylene glycol)-based hydrogels by introducing UPy groups into amphiphilic copolymers in order to form strong hydrogen bonds that act as physical cross-links. Leibler's group^{7, 8} reported the design of hydrogen-bonded synthetic rubbers using renewable starting materials that exhibit both self-healing and thermoreversible behavior. Kornfield and co-workers¹⁵ utilized charge-assisted hydrogen bonding to design


complementary low molecular weight telechelic precursors that self-assemble to form high molecular weight 'megasupramolecules' in non-polar media. This approach confers a significant thickening effect, while irreversible shear-induced degradation can be avoided via a 'self-healing' mechanism. Hence these hydrogen-bonded nanostructures significantly out-perform high molecular weight polyisobutylene additives as anti-misting agents for jet fuel. Similar hydrogen bonding interactions between imidazole and carboxylic acid groups have been exploited for the formation of hydrogels with enhanced mechanical properties,¹⁶ while Ikkala and co-workers^{17, 18} reported exquisite control over multiple length scales via hydrogen bonding-mediated self-assembly of a 1:1 methanesulfonic acid/poly(4-vinylpyridine) using varying amounts of pentadecylphenol. The discovery of living anionic polymerization,^{19, 20} and more recently the development of reversible-deactivation radical polymerization techniques,^{21, 22} has enabled the design of a remarkably wide range of well-defined functional block copolymers, which exhibit spontaneous self-assembly either in the bulk^{23, 24} and/or in solution.^{25, 26} For example, the formation of diblock copolymer *spheres* in solvents that are selective for one of the two blocks has been known for more than fifty years.²⁷ In 1999, Bates and co-workers²⁸ reported that aqueous dispersions of highly anisotropic poly(ethylene oxide)-polybutadiene *worms* formed free-standing viscoelastic gels above a certain critical copolymer concentration. Since this seminal study, block copolymer worms have been evaluated for drug delivery,^{29, 30} as sterilizable hydrogels³¹ for 3D cell culture³² and stem cell storage,³³ for

^a Chemistry Department, University of Sheffield, Dainton Building, Brook Hill, Sheffield, South Yorkshire, S3 7HF, UK.

^b Present address: Aston Institute of Materials Research (AIMR), Aston University, Aston Triangle, Birmingham, B4 7ET, UK.

Electronic Supplementary Information (ESI) available: Experimental section; Kinetic study; Assigned ¹H NMR spectra; GPC data; Additional TEM images; Additional rheological data; IR spectra; Theoretical calculations for hydrogen bonding dimers; Equilibrium configuration of the methyl acetate dimer; SAXS model. See DOI: 10.1039/x0xx00000x



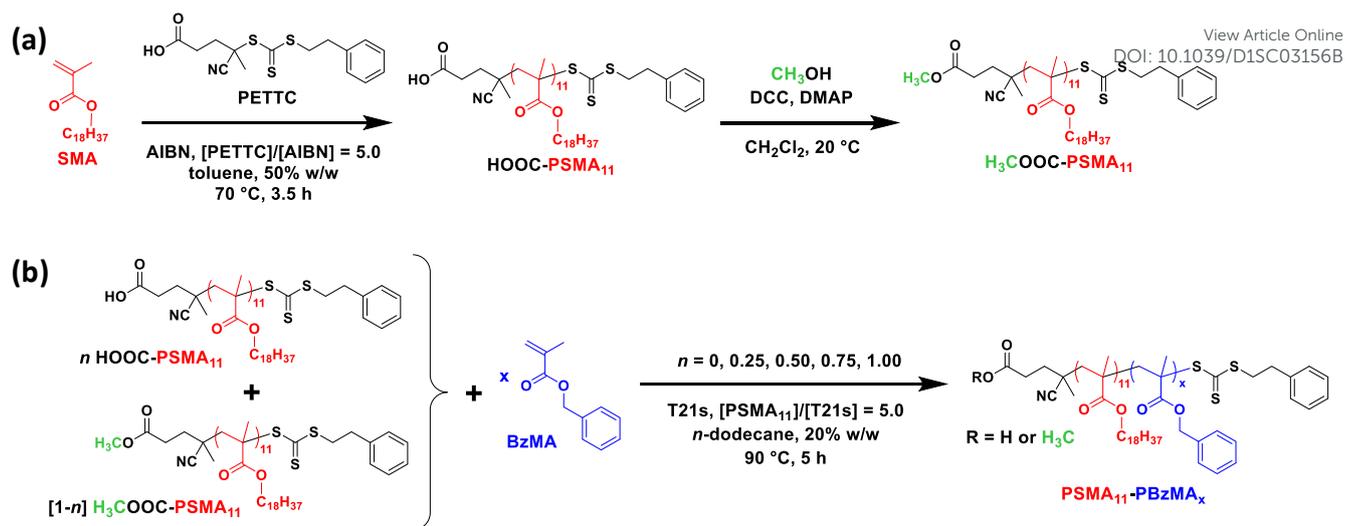

Scheme 1. (a) Synthesis of HOOC-PSMA₁₁ macro-CTA via RAFT solution polymerization of SMA in toluene at 70 °C and the subsequent preparation of its methyl ester analogue, H₃COOC-PSMA₁₁ macro-CTA, via esterification. (b) Synthesis of a series of PSMA₁₁-PBzMA_x diblock copolymer nano-objects via RAFT dispersion polymerization of BzMA in *n*-dodecane at 90 °C using various binary mixtures of HOOC-PSMA₁₁ and H₃COOC-PSMA₁₁ macro-CTAs.


cryopreservation of red blood cells,³⁴ as superflocculants for micrometer-sized particles,³⁵ for viscosity modification,³⁶ for reinforcement of latex films³⁷ and as model Pickering emulsifiers.^{38, 39} This sub-field has been reviewed by Davis and co-workers⁴⁰ and more recently by Tian *et al.*⁴¹

Traditionally, block copolymer self-assembly in solution has been achieved by post-polymerization processing techniques such as a solvent switch or thin film rehydration, which usually only enable the preparation of rather dilute copolymer dispersions.^{25, 42, 43} In contrast, polymerization-induced self-assembly (PISA) enables the rational synthesis of block copolymer nano-objects at relatively high copolymer concentrations (up to 50% w/w).⁴⁴⁻⁴⁷ In particular, reversible addition-fragmentation chain transfer (RAFT) polymerization^{48, 49} has enabled the efficient PISA synthesis of a wide range of functional block copolymer spheres, worms or vesicles in aqueous,⁵⁰⁻⁵³ alcoholic⁵⁴⁻⁵⁹ or non-polar⁶⁰⁻⁶⁴ media. Typically, the worm morphology occupies rather narrow phase space.⁶⁰⁻⁶³ However, Rieger and co-workers recently designed a functional RAFT agent in order to place bis-urea 'stickers' within the core-forming block; introducing this hydrogen bonding motif enables the worm phase space to be significantly expanded for an aqueous PISA formulation.⁶⁵ Alternatively, constructing an appropriate pseudo-phase diagram based on PISA syntheses provides a reliable means of targeting the otherwise elusive worm morphology.⁵⁹⁻⁶³ This systematic approach has led directly to many more examples of well-defined block copolymer worms being reported.⁶⁶⁻⁷⁰ An additional method of controlling nanoparticle morphology during PISA involves the judicious selection of chain-end functionality.⁷¹ It is now recognized that many PISA formulations based on RAFT dispersion polymerization afford *thermoresponsive* diblock copolymer worms⁷² in either aqueous,^{31, 73} alcoholic,⁷⁴ or non-polar^{67, 68} media. In particular, heating a dispersion of poly(lauryl methacrylate)-poly(benzyl methacrylate) worms in *n*-dodecane induces a worm-to-sphere morphology transition,


which can be fully reversible if conducted at sufficiently high copolymer concentration.⁶⁷

The present work focuses on diblock copolymer worms that form free-standing gels at sufficiently high copolymer concentration owing to a percolating network arising from multiple inter-worm contacts.⁷⁵ Hydrogen bonding is particularly strong in non-polar media,⁷⁶ with one well-known example of such a non-covalent interaction being the dimerization of acetic acid in benzene.⁷⁷ In principle, the synthesis of diblock copolymer worms via RAFT-mediated PISA in non-polar media provides an opportunity to form stronger gels by introducing appropriate inter-worm attractive forces. In this context, it is noteworthy that selecting an appropriate RAFT chain transfer agent (CTA) enables carboxylic acid groups to be conveniently introduced at the end of every steric stabilizer chain (see Scheme 1). For methacrylates this RAFT CTA can typically be either a dithioester or trithiocarbonate. For the purposes of the present work, a carboxylic acid-functional trithiocarbonate, 4-cyano-4-(2-phenylethanesulfanylthiocarbonyl)sulfanylpentanoic acid (PETTC), was utilized. Thus, when the copolymer concentration exceeds the critical gelation concentration, this should lead to the formation of carboxylic acid dimers at the point where neighboring worms just touch each other to form the 3D percolating network.⁷⁵ Moreover, synthesis of the equivalent diblock copolymer worms using a methyl ester-based RAFT CTA offers a suitable control gel for which no inter-worm hydrogen bonding interactions are possible. Thus, systematic variation of the carboxylic acid/methyl ester molar ratio should enable modulation of the inter-worm interactions and hence provide fine control over the physical properties of the worm gels. Alternatively, the thermo-responsive nature of such diblock copolymer worms can be exploited to adjust the worm gel strength. In principle, this is achieved by heating concentrated dispersions of carboxylic acid- and methyl ester-functionalized worms up to 110 °C in turn to induce a worm-to-sphere transition in each case, followed by mixing the resulting hot

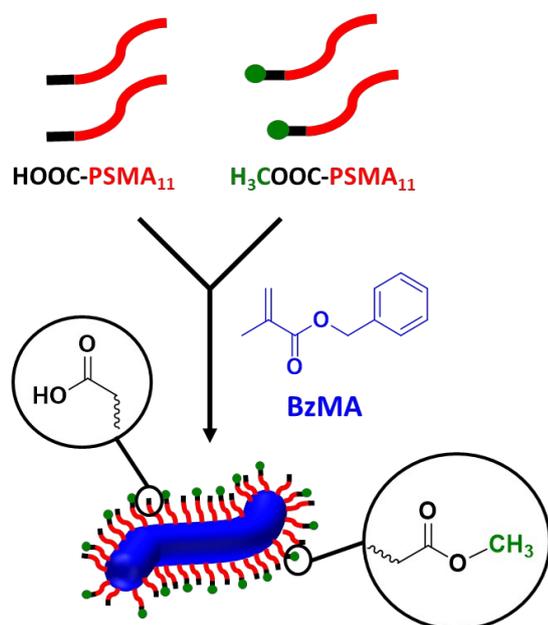

Route 1: *in situ* PISA approach

Route 2: post-polymerization processing strategy

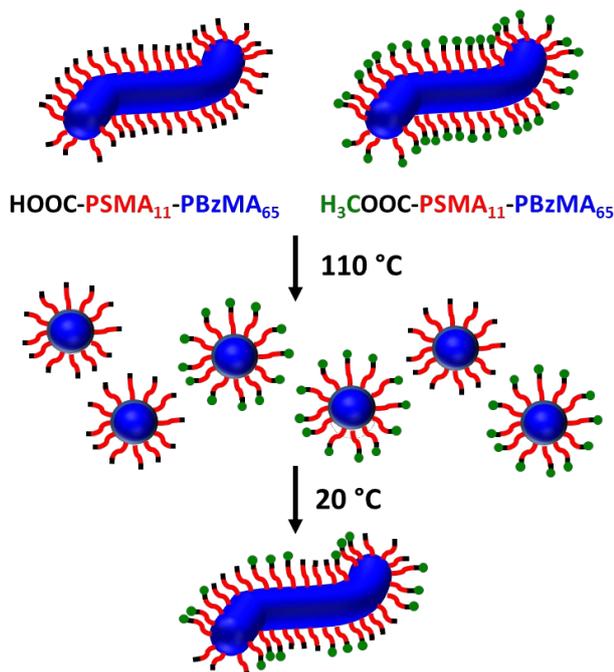View Article Online
DOI: 10.1039/D1SC03156B

Scheme 2. Schematic representation of the two synthetic routes used herein to prepare the two series of PSMA-PBzMA worms containing varying proportions of carboxylic acid end-groups. Both routes are based on the principle of entropic mixing. Route 1 utilizes a binary mixture of HOOC-PSMA₁₁ and H₃COOC-PSMA₁₁ precursors during the RAFT dispersion polymerization of BzMA; this approach results in a statistical distribution of carboxylic acid end-groups located at the outer surface of each sterically-stabilized worm. Route 2 involves heating two 'masterbatch' 20% w/w dispersions comprising HOOC-PSMA₁₁-PBzMA₆₅ and H₃COOC-PSMA₁₁-PBzMA₆₅ worm gels up to 110 °C to induce a worm-to-sphere transition (and concomitant degelation) in each case. These two free-flowing fluids of spherical nanoparticles were then mixed together in various proportions at this temperature to produce the desired range of carboxylic acid/methyl ester molar ratios. On cooling to 20 °C, a sphere-to-worm transition occurs via 1D stochastic fusion of multiple (mixed) spheres to produce 'hybrid' segmented worms comprising *spatially-localized* patches of steric stabilizer chains bearing carboxylic acid end-groups.

free-flowing fluids together in varying proportions. Subsequent cooling leads to the formation of a series of 'hybrid' segmented worm gels via stochastic 1D fusion of the carboxylic acid- and methyl ester-functionalized spheres (see Scheme 2). This complementary approach should also enable the worm gel strength to be tuned over a wide range. Herein we examine these new concepts by performing rheological measurements on well-characterized diblock copolymer worm dispersions in a model high boiling point solvent, *n*-dodecane.

Results and discussion

Synthesis of HOOC-PSMA₁₁ and H₃COOC-PSMA₁₁ homopolymer precursors via RAFT solution polymerization of SMA

A kinetic study of the RAFT solution polymerization of SMA in toluene at 70 °C was conducted by periodically removing aliquots of the reaction mixture for analysis over a 7 h period (see Figure S1). Monomer conversions were calculated using ¹H NMR spectroscopy by comparing the integrated monomer vinyl proton signals at 5.6 and 6.2 ppm with the two oxymethylene protons assigned to the monomer/polymer at 4.0 ppm. A monotonic increase in monomer conversion with polymerization time was observed (see Figure S1a). There are

two distinct regimes: initial relatively slow polymerization for the first 100 min, followed by a faster rate of polymerization that obeys first-order kinetics with respect to SMA, as judged by the linear semi-logarithmic plot. The GPC curves shown in Figure S1b were analyzed using a refractive index detector and poly(methyl methacrylate) calibration standards: a linear evolution in M_n with conversion was observed (see Figure S1c) and a relatively narrow molecular weight distribution was obtained for the final PSMA homopolymer ($M_n = 3\ 100\ \text{g mol}^{-1}$; $M_w/M_n = 1.18$; 93% conversion). Informed by this kinetic study, SMA was polymerized on a 40-gram scale under the same conditions and quenched after 6 h (76% conversion) to ensure retention of the trithiocarbonate-based RAFT chain-ends. After purification via precipitation into excess ethanol, the resulting HOOC-PSMA macro-CTA had a mean degree of polymerization (DP) of 11 as judged by ¹H NMR spectroscopy, while THF GPC analysis indicated an M_n of 5 400 g mol⁻¹ and an M_w/M_n of 1.11. Esterification of this HOOC-PSMA₁₁ precursor using excess methanol produced the corresponding H₃COOC-PSMA₁₁ macro-CTA (see Scheme 1a). ¹H NMR spectroscopy confirmed successful end-group derivatization: comparison of the integrated terminal methyl ester proton signal at 3.7 ppm to that of the oxymethylene proton signal assigned to the SMA repeat units at 4.0 ppm indicated that the degree of



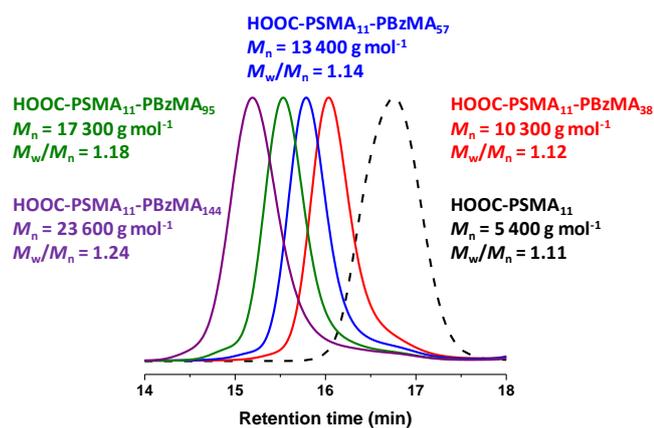


Figure 1. THF GPC curves recorded for selected HOOC-PSMA₁₁-PBzMA_x diblock copolymers prepared via RAFT dispersion polymerization of BzMA in *n*-dodecane at 90 °C using the HOOC-PSMA₁₁ precursor. Conditions: 20% w/w solids, [HOOC-PSMA₁₁]/[T21S] molar ratio = 5.0, reaction time = 5 h. The GPC curve recorded for the HOOC-PSMA₁₁ homopolymer precursor (black dashed curve) is also shown as a reference.

esterification of the carboxylic acid end-groups was 97% (see Figure S2). Importantly, this synthetic strategy produces two chemically identical steric stabilizer blocks that differ only in the nature of their end-groups. Indeed, the THF GPC curves recorded for these two precursors overlay almost precisely (see Figure S3).

Synthesis of HOOC-PSMA₁₁-PBzMA_x and H₃COOC-PSMA₁₁-PBzMA_x diblock copolymer nano-objects

A series of PSMA₁₁-PBzMA_x diblock copolymer nano-objects were synthesized via RAFT dispersion polymerization of BzMA using the HOOC-PSMA₁₁ precursor at 90 °C in *n*-dodecane (see Scheme 1b, where $n = 1.00$). In all cases, the final BzMA conversion was at least 95% and THF GPC analysis indicated that narrow molecular weight distributions ($M_w/M_n < 1.25$) were obtained when targeting PBzMA DPs up to 150 (see Figure 1). Depending on the target PBzMA DP, this series of HOOC-PSMA₁₁-PBzMA_x diblock copolymers self-assembled *in situ* to form either spherical ($x \leq 38$), worm-like ($52 \leq x \leq 65$) or vesicular ($x \geq 95$) morphologies (see Figure S4). These observations are in generally good agreement with those reported for a series of closely-related PSMA₁₃-PBzMA_x diblock copolymer nano-objects prepared in mineral oil using a dithiobenzoate-based RAFT agent.⁶³ Importantly, the corresponding series of H₃COOC-PSMA₁₁-PBzMA_x diblock copolymers prepared using the same PISA protocol also formed pure worms for $53 \leq x \leq 65$ (see Figure S5). Both the carboxylic acid and methyl ester end-groups are located on the outer surface of these sterically-stabilized worms (see Scheme 2). Thus, this offers an unprecedented opportunity to modulate the physical properties of the free-standing worm gels that are formed as a result of multiple inter-worm contacts.⁷⁵ More specifically, conducting a series of PISA syntheses utilizing a *binary mixture* of HOOC-PSMA₁₁ and H₃COOC-PSMA₁₁ macro-CTAs enables systematic variation of the carboxylic acid/methyl ester molar ratio. In principle, this should enable fine-tuning of the inter-worm interactions, which in turn influence the physical properties of the worm gels.

Tuning the properties of hydrogen-bonded PSMA-PBzMA worm gels

DOI: 10.1039/D1SC03156B

Firstly, a series of PSMA₁₁-PBzMA₆₅ worms comprising varying amounts of carboxylic acid and methyl ester end-groups were prepared *in situ* via PISA by utilizing a binary mixture of the HOOC-PSMA₁₁ and H₃COOC-PSMA₁₁ precursors (see **Route 1** in Scheme 2). Systematic variation of the HOOC-PSMA₁₁/H₃COOC-PSMA₁₁ molar ratio enabled the proportion of carboxylic acid end-groups to be fine-tuned from 0 to 100 mol% for a series of five worm gels. Alternatively, a series of five PSMA₁₁-PBzMA₆₅ worm gels comprising steric stabilizer chains bearing carboxylic acid end-groups were prepared via a post-polymerization processing strategy whereby two separate 'masterbatches' comprising 20% w/w dispersions of HOOC-PSMA₁₁-PBzMA₆₅ and H₃COOC-PSMA₁₁-PBzMA₆₅ worm gels were heated to 110 °C (see **Route 2** in Scheme 2). In both cases, this thermal treatment induced a worm-to-sphere transition with concomitant *in situ* degelation.⁶⁷ The resulting two free-flowing fluids were subsequently mixed together in various proportions at this temperature and then each dispersion was allowed to cool to ambient temperature to induce a sphere-to-worm transition, with the resulting copolymer dispersion forming a free-standing gel at 20 °C. Assuming that entropic mixing occurs (rather than self-sorting), the stochastic 1D fusion of multiple (mixed) spheres is expected to produce a series of 'hybrid' segmented worms comprising *spatially-localized* patches of carboxylic acid end-groups.

Five worm gels were prepared using **Route 1** and **Route 2**, respectively. In each case, the mole fraction of carboxylic acid end-groups (n) was adjusted to be 0, 0.25, 0.50, 0.75 and 1.00. Importantly, transmission electron microscopy (TEM) studies confirmed that a pure worm morphology was obtained in each case (see Figure 2). Moreover, each of these ten copolymer dispersions formed relatively transparent free-standing worm gels at 20 °C (see Figure 2, inset images). Each of the 20% w/w copolymer dispersions prepared by either **Route 1** or **Route 2** exhibit a pure worm morphology and formed free-standing gels at ambient temperature. The physical properties of these worm gels were assessed via oscillatory rheology studies. Angular frequency sweeps from 0.1 to 100 rad s⁻¹ were performed at 25 °C using a fixed strain amplitude of 1.0% (see Figure S6). Importantly, the thermal history of these worm gels was removed by heating to 110 °C, then allowing to cool to 25 °C over a 24 h period before conducting the angular frequency sweeps.⁷³ The storage modulus (G') remained significantly greater than the loss modulus (G'') over the entire range of angular frequencies, thus indicating that each dispersion was a true gel. Furthermore, these worm gels exhibit linear viscoelasticity in this region, as judged by the relatively weak angular frequency dependence for G' . For both series of worm gels, substantially higher G' values were obtained when increasing the carboxylic acid end- group content (see Figure 3a). Thus, a 20% w/w worm gel comprising solely HOOC-PSMA₁₁-PBzMA₆₅ exhibited a G' of ~114 kPa, whereas that for a 20% w/w worm gel comprising solely H₃COOC-PSMA₁₁-PBzMA₆₅ was ~4.5 kPa. This approximate 25-fold increase in G' suggests




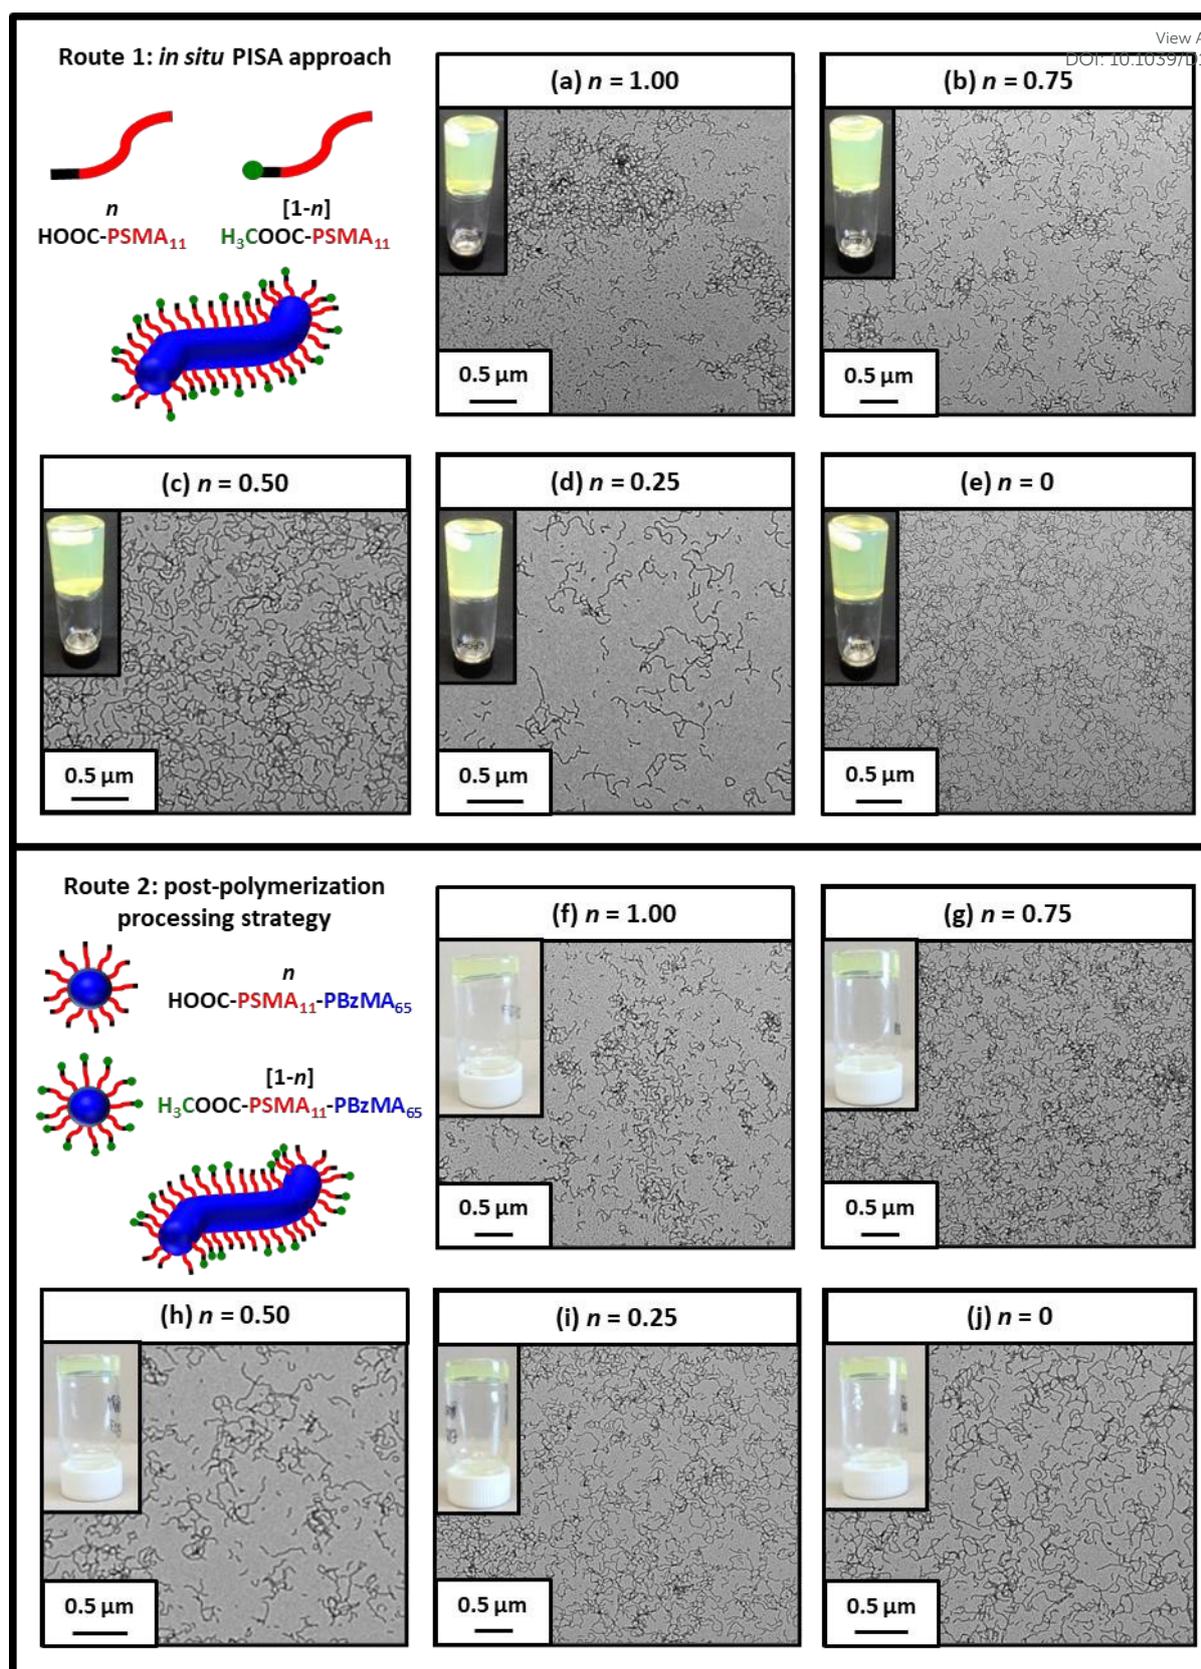


Figure 2. Representative transmission electron micrographs recorded for 0.10% w/w dispersions of the ten examples of PSMA-PBzMA diblock copolymer worms prepared using **Route 1** and **Route 2** in this study (see Scheme 2). Insets show digital photographs recorded for the corresponding ten worm gels at 10% w/w solids. This so-called tube inversion test confirms their free-standing nature at ambient temperature.

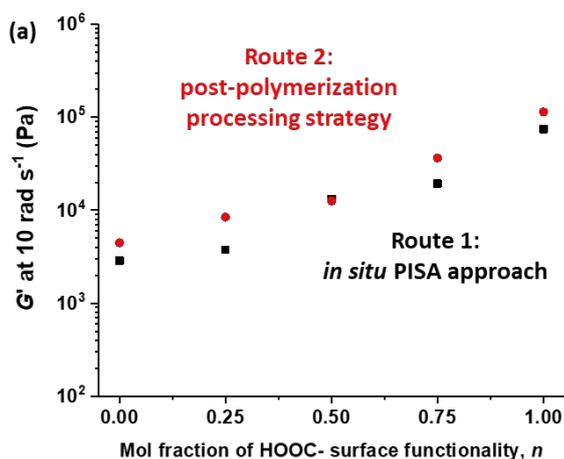

(b) HOOC-PSMA₁₁-PBzMA₆₅ worms

20 12 10 5 4 3 2 % w/w

(c) H₃COOC-PSMA₁₁-PBzMA₆₅ worms

20 15 12 11 10 9 % w/w



Figure 3. (a) Effect of varying the mole fraction of carboxylic acid end-groups on the storage modulus, G' , for 20% w/w PSMA₁₁-PBzMA₆₅ worm gels prepared via **Routes 1 and 2** [G' data recorded at an angular frequency of 10 rad s⁻¹]. Digital images recorded for HOOC-PSMA₁₁-PBzMA₆₅ (b) and H₃COOC-PSMA₁₁-PBzMA₆₅ (c) worms dispersed in *n*-dodecane at various copolymer concentrations.

significantly greater inter-worm interactions for the former gel. Interestingly, the worm gels prepared via **Route 2** typically exhibit higher G' values than the equivalent worm gels prepared via **Route 1**. In principle, this suggests that a relatively high local concentration of carboxylic acid end-groups favors the formation of multiple carboxylic acid dimers at the point(s) of contact between neighboring worms. However, in principle the G' values obtained for the two pairs of worm gels containing no carboxylic acid groups ($n = 0$) and solely carboxylic acid groups ($n = 1.00$) should be identical. Thus the observed difference between each pair of measurements shown in Figure 3a most likely indicates the experimental uncertainty in these rheological experiments (estimated to be 30-50%). In this context, it is worth emphasizing that the 25-fold boost in G' is much larger than this experimental uncertainty.

Temperature-dependent oscillatory rheology studies provide further evidence for hydrogen bonding interactions between carboxylic acid-functionalized worms (see Figure S7). The purpose of these experiments was to determine the critical gelation temperature (CGT), which is the temperature above which the dispersion is no longer a gel (i.e. where G'' exceeds G'). A worm gel containing solely HOOC-PSMA₁₁-PBzMA₆₅


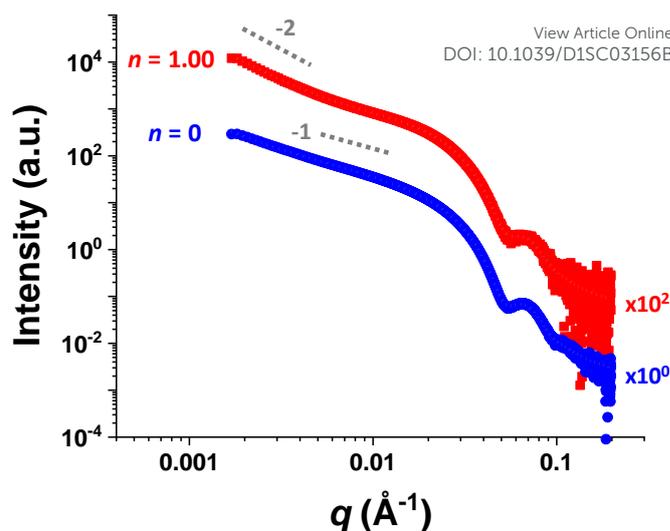


Figure 4. Small-angle X-ray scattering (SAXS) patterns recorded for 1.0% w/w dispersions of purely HOOC-PSMA₁₁-PBzMA₆₅ worms ($n = 1.00$, red squares) and purely H₃COOC-PSMA₁₁-PBzMA₆₅ worms ($n = 0$, blue circles) in *n*-dodecane. Indicative gradients of -1 and -2 are shown as a guide to the eye. Data fits using an established worm-like micelle model⁷⁸ are shown as dotted white lines within the experimental data. A pronounced upturn at low q is observed for the upper pattern, indicating significantly stronger inter-worm interactions in this case. This is consistent with the postulated hydrogen-bonding interactions between neighboring worms (see Scheme 3). (N.B. The $n = 1.00$ pattern is offset by a factor of 10^2 relative to the $n = 0$ pattern for the sake of clarity).

exhibited a CGT of 92 °C, whereas the CGT of H₃COOC-PSMA₁₁-PBzMA₆₅ worm gel containing no carboxylic acid groups was significantly lower (41 °C). Similarly, a significant difference is observed for the critical gelation concentration (CGC), which is defined as the minimum concentration at which a free-standing gel can be obtained (see Figure 3b and 3c). We have previously shown that reducing the copolymer concentration of worm gels leads to degelation due to the reduction in the number of inter-worm contacts that form the gel network.⁷⁵ It is thus highly likely that reducing the copolymer concentration of the present worm dispersions would result in fewer inter-worm hydrogen bonds and hence weaker gels or macroscopic degelation. The CGC for the HOOC-PSMA₁₁-PBzMA₆₅ worm gel ($n = 1.00$) is 2-3% w/w, whereas that for the H₃COOC-PSMA₁₁-PBzMA₆₅ worm gel ($n = 0$) is ~10% w/w. For the former worm gel, the significantly lower CGC and higher CGT values observed are attributed to the additional hydrogen bonding interactions between adjacent HOOC-PSMA₁₁-PBzMA₆₅ worms, which act to reinforce the 3D gel network.⁷⁹

For HOOC-PSMA₁₁-PBzMA₆₅ ($n = 1.00$) and H₃COOC-PSMA₁₁-PBzMA₆₅ ($n = 0$) dispersions, SAXS patterns were recorded at a copolymer concentration of 1.0% w/w (see Figure 4). In both cases, an approximate $I(q) \sim q^{-1}$ dependence was observed in the low q region, which is consistent with a well-defined worm-like morphology.⁸⁰ Moreover, the local minima observed at high q indicate that these two types of worms exhibit the same mean worm core cross-sectional diameter. Indeed, fitting these data to a well-established worm-like micelle model⁷⁸ confirmed that the mean overall worm thickness ($T_{\text{worm}} = 2R_{\text{wc}} + 4R_{\text{g}}$, where R_{wc} is the mean worm core radius and R_{g} is the radius of gyration of the stabilizer chains) for these two samples were 16.8 and 16.6 nm, respectively. Furthermore, the mean worm length (L_{worm})



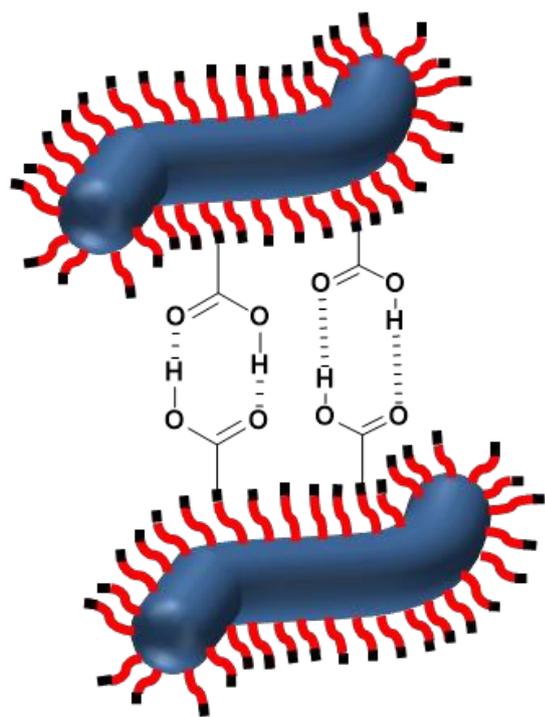

Scheme 3. Schematic representation of the formation of hydrogen-bonded dimers between the carboxylic acid-functionalized worms described in this study.

was determined to be approximately 900 nm for both worms exhibit a pronounced upturn in X-ray scattering intensity dispersions. However, the HOOC-PSMA₁₁-PBzMA₆₅ ($n = 1.00$) at low q compared to the H₃COOC-PSMA₁₁-PBzMA₆₅ ($n = 0$) worms. An $I(q) = Bq^{-P}$ relationship was incorporated into the scattering model to account for this effect, whereby higher P values indicate a steeper slope in the low q region. Indeed, a P value of 1.95 was determined for the HOOC-PSMA₁₁-PBzMA₆₅ ($n = 1.00$) worms, whereas the H₃COOC-PSMA₁₁-PBzMA₆₅ ($n = 0$) worms have a P value of only 1.63. This suggests significantly stronger inter-worm interactions for the former copolymer dispersion. More specifically, we hypothesize that such interactions involve the formation of hydrogen-bonded carboxylic acid dimers (see Scheme 3).

Recently we reported⁷⁵ that, to a reasonable first approximation, the gelation behavior of block copolymer worms can be rationalized in terms of the percolation theory developed by Chatterjee for polydisperse rods.⁸¹ This suggests that multiple inter-worm contacts (rather than worm entanglements, which have been invoked to account for the gelation behavior observed for surfactant-based worms⁸²⁻⁸⁴) are sufficient to form a 3D gel network. Furthermore, the critical worm volume fraction, φ_c , required for macroscopic gelation scales with the mean worm radius, R , and the weight-average worm length, L_w according to the simple relationship $\varphi_c \sim R/L_w$.⁷⁵ Fitting the SAXS data shown in Figure 4 to a well-established worm-like micelle model⁷⁸ confirms that the mean dimensions (i.e. R and L_w) for worms prepared using the carboxylic acid-based RAFT agent alone ($n = 1.00$) and the methyl ester-based RAFT agent alone ($n = 0$) are almost identical (see above). Thus, percolation theory predicts that these two types of worm gel should exhibit essentially the same behavior.

However, the rheological data shown in Figure 3a and digital images shown in Figure 3b and 3c clearly indicate substantial differences in both the CGC (or φ_c) and the CGT. This is consistent with additional attractive forces operating between neighboring worms, which leads to significantly stronger inter-worm interactions.

Spectroscopic investigations of hydrogen bonding

We now present indirect spectroscopic evidence that such non-covalent interactions actually involve carboxylic acid dimer formation (see Scheme 3). Conventional hydrogen bonds such as those formed between water molecules exhibit enthalpies of dissociation of ~ 23 kJ mol⁻¹ at 298 K.⁸⁵ However, the enthalpy of dissociation for carboxylic acid dimers is significantly stronger, typically ~ 34 kJ mol⁻¹ for acetic acid dimers in benzene at 298 K.⁸⁶ In principle, the presence of hydrogen-bonded dimers could be confirmed by observing the splitting of the acid carbonyl stretching vibration into an IR-active and a Raman active component or by observing frequency shifts between the carboxylic acid-functionalized worms and the ester-functionalized worms. Unfortunately, obtaining direct spectroscopic evidence for the formation of carboxylic acid dimers between neighboring block copolymer worms in n -dodecane is not experimentally feasible for three reasons. First, there is only one carboxylic acid end-group per block copolymer chain. On the other hand, each chain contains on average 76 methacrylic ester repeat units, which absorb IR radiation at a very similar frequency (approximately 1700 cm⁻¹ for carboxylic acids and 1720-1740 cm⁻¹ for esters⁸⁷). Second, unless the worms are aligned under flow, only a rather small proportion of carboxylic acid end-groups are expected to be involved in the formation of carboxylic acid dimers between neighboring worms when forming a percolating 3D gel network via inter-worm contacts.⁷⁵ Finally, carboxylic acid dimer formation within individual worms is not spectroscopically distinguishable from that between neighboring worms, although only the latter species contributes to stronger worm gels.

Nevertheless, indirect evidence for carboxylic acid dimer formation can be obtained by FT-IR spectroscopy studies of each of the two PSMA₁₁ precursors dissolved in n -dodecane (see Figure S8). In this case, there is one carboxylic acid end-group per eleven methacrylic ester repeat units, which makes it much easier to observe IR signatures arising from the former species. Thus, by working at a relatively high concentration (50% w/w), a wavenumber shift of approximately -10 cm⁻¹ can be observed in the carbonyl region, which is in semi-quantitative agreement with theoretical calculations that predict a more pronounced red shift for carboxylic acid dimers compared to ester dimers (see details in the Supporting Information). Thus there is reasonable experimental and theoretical evidence to suggest that carboxylic acid-functionalized worms should exhibit much stronger hydrogen bonding interactions compared to ester-functionalized worms. This is expected to boost the bulk modulus observed for the former worm gels, as observed in the rheological studies reported herein.



Conclusions

We report two complementary entropic mixing strategies for boosting the bulk modulus of sterically-stabilized poly(stearyl methacrylate)-poly(benzyl methacrylate) diblock copolymer worm gels via hydrogen bonding interactions. This is achieved simply by introducing carboxylic acid groups at the end of the poly(stearyl methacrylate) stabilizer chains, which leads to the formation of carboxylic acid dimers between neighboring worms in non-polar media. Unlike many other literature examples of hydrogen-bonded polymer systems, introducing this structural motif involves minimal synthetic effort because the RAFT polymerization chemistry employed to prepare these diblock copolymer worms typically utilizes carboxylic acid-based RAFT agents. Thus, using binary mixtures of carboxylic acid- and methyl ester-functionalized poly(stearyl methacrylate) stabilizers for the RAFT dispersion polymerization of benzyl methacrylate (**Route 1**) enables the storage gel modulus, G' , to be systematically varied from ~ 4.5 kPa up to ~ 114 kPa. A similar variation in gel strength can be achieved by exploiting the thermoreversible worm-to-sphere transition exhibited by such worm gels. Thus, mixing concentrated dispersions of free-flowing carboxylic acid- and methyl ester-functionalized spheres together at 110 °C leads to the formation of 'hybrid' segmented worms on cooling to ambient temperature via stochastic 1D fusion of multiple spheres (**Route 2**). Moreover, SAXS studies indicate that significantly stronger inter-worm interactions can be achieved when using a carboxylic acid-based RAFT agent for such worm gel syntheses, while rheological studies indicate both a significant reduction in critical gelation concentration (from approximately 10% w/w to 2-3% w/w) and a substantial increase in critical gelation temperature (from 41 °C to 92 °C). In summary, this study highlights how the introduction and judicious modulation of non-covalent interactions can be used to tune the physical properties of block copolymer worm gels, thus providing significant improvements in gel strength, gelation efficiency and gel cohesion.

Author Contributions

M.J.D. and S.P.A. conceived the project. E.R. performed all syntheses and obtained NMR, GPC, rheology and FT-IR data. M.J.D. performed TEM and SAXS analyses. M.F.A.H. conducted quantum chemical calculations. All co-authors contributed to the writing, reviewing and editing of this manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

S.P.A. acknowledges an EPSRC Established Career Fellowship (EP/R003009/1). The Leverhulme Trust is also thanked for post-doctoral funding of M.J.D. (RPG-2016-330). Csilla György is thanked for her kind assistance in acquiring ^1H NMR spectra. Dr.

Svetomir Tzokov at the University of Sheffield Biomedical Science Electron Microscopy Suite is thanked for TEM assistance. All staff on the I22 beamline at Diamond Light Source are thanked for help and advice during SAXS data collection (experiment no. SM21776).

Notes and references

‡ This M_n value is somewhat larger than that obtained at 93% monomer conversion during the kinetic study (see Figure S1c). This is because a purification via precipitation into excess ethanol removes lower molecular weight PSMA oligomers, which remain soluble in this solvent.

1. W. M. Latimer and W. H. Rodebush, *Journal of the American Chemical Society*, 1920, **42**, 1419-1433.
2. C. G. Cannon, *Spectrochimica Acta*, 1958, **10**, 341-368.
3. P. A. Kollman and L. C. Allen, *Chemical Reviews*, 1972, **72**, 283-303.
4. C. B. Aakeröy and K. R. Seddon, *Chemical Society Reviews*, 1993, **22**, 397-407.
5. J. D. Watson and F. H. C. Crick, *Nature*, 1953, **171**, 737-738.
6. R. P. Sijbesma, F. H. Beijer, L. Brunsveld, B. J. B. Folmer, J. H. K. K. Hirschberg, R. F. M. Lange, J. K. L. Lowe and E. W. Meijer, *Science*, 1997, **278**, 1601-1604.
7. P. Cordier, F. Tournilhac, C. Soulié-Ziakovic and L. Leibler, *Nature*, 2008, **451**, 977.
8. D. Montarnal, F. Tournilhac, M. Hidalgo, J.-L. Couturier and L. Leibler, *Journal of the American Chemical Society*, 2009, **131**, 7966-7967.
9. M. Guo, L. M. Pitet, H. M. Wyss, M. Vos, P. Y. W. Dankers and E. W. Meijer, *Journal of the American Chemical Society*, 2014, **136**, 6969-6977.
10. O. J. G. M. Goor, S. I. S. Hendrikse, P. Y. W. Dankers and E. W. Meijer, *Chemical Society Reviews*, 2017, **46**, 6621-6637.
11. L. R. Rieth, R. F. Eaton and G. W. Coates, *Angewandte Chemie International Edition*, 2001, **40**, 2153-2156.
12. K. Yamauchi, J. R. Lizotte and T. E. Long, *Macromolecules*, 2003, **36**, 1083-1088.
13. K. E. Feldman, M. J. Kade, E. W. Meijer, C. J. Hawker and E. J. Kramer, *Macromolecules*, 2009, **42**, 9072-9081.
14. X. Chang, C. Wang, G. Shan, Y. Bao and P. Pan, *Langmuir*, 2020, **36**, 956-965.
15. M.-H. Wei, B. Li, R. L. A. David, S. C. Jones, V. Sarohia, J. A. Schmitgal and J. A. Kornfield, *Science*, 2015, **350**, 72.
16. X. N. Zhang, Y. J. Wang, S. Sun, L. Hou, P. Wu, Z. L. Wu and Q. Zheng, *Macromolecules*, 2018, **51**, 8136-8146.
17. J. Ruokolainen, R. Mäkinen, M. Torkkeli, T. Mäkelä, R. Serimaa, G. t. Brinke and O. Ikkala, *Science*, 1998, **280**, 557-560.
18. O. Ikkala and G. ten Brinke, *Science*, 2002, **295**, 2407-2409.
19. M. Szwarc, *Nature*, 1956, **178**, 1168-1169.
20. M. Szwarc, M. Levy and R. Milkovich, *Journal of the American Chemical Society*, 1956, **78**, 2656-2657.
21. M. Destarac, *Polymer Chemistry*, 2018, **9**, 4947-4967.
22. W. A. Braunecker and K. Matyjaszewski, *Progress in Polymer Science*, 2007, **32**, 93-146.
23. F. S. Bates, *Science*, 1991, **251**, 898.
24. F. S. Bates and G. H. Fredrickson, *Physics Today*, 1999, **52**, 32-38.
25. Y. Mai and A. Eisenberg, *Chemical Society Reviews*, 2012, **41**, 5969-5985.



26. S. Förster and M. Antonietti, *Advanced Materials*, 1998, **10**, 195-217.
27. D. W. J. Osmond, 1962, GB Patent 893,429.
28. Y. Y. Won, H. T. Davis and F. S. Bates, *Science*, 1999, **283**, 960-963.
29. K. Younghoon, D. Paul, A. C. David and E. D. Dennis, *Nanotechnology*, 2005, **16**, S484.
30. B. Karagoz, L. Esser, H. T. Duong, J. S. Basuki, C. Boyer and T. P. Davis, *Polymer Chemistry*, 2014, **5**, 350-355.
31. A. Blanazs, R. Verber, O. O. Mykhaylyk, A. J. Ryan, J. Z. Heath, C. W. I. Douglas and S. P. Armes, *Journal of the American Chemical Society*, 2012, **134**, 9741-9748.
32. K. A. Simon, N. J. Warren, B. Mosadegh, M. R. Mohammady, G. M. Whitesides and S. P. Armes, *Biomacromolecules*, 2015, **16**, 3952-3958.
33. I. Canton, N. J. Warren, A. Chahal, K. Amps, A. Wood, R. Weightman, E. Wang, H. Moore and S. P. Armes, *ACS Central Sci.*, 2016, **2**, 65-74.
34. D. E. Mitchell, J. R. Lovett, S. P. Armes and M. I. Gibson, *Angew. Chem.-Int. Edit.*, 2016, **55**, 2801-2804.
35. N. J. W. Penfold, Y. Ning, P. Verstraete, J. Smets and S. P. Armes, *Chemical Science*, 2016, **7**, 6894-6904.
36. M. J. Derry, O. O. Mykhaylyk and S. P. Armes, *Angewandte Chemie International Edition*, 2017, **56**, 1746-1750.
37. R. Albigès, P. Klein, S. Roi, F. Stoffelbach, C. Creton, L. Bouteiller and J. Rieger, *Polymer Chemistry*, 2017, **8**, 4992-4995.
38. K. L. Thompson, L. A. Fielding, O. O. Mykhaylyk, J. A. Lane, M. J. Derry and S. P. Armes, *Chemical Science*, 2015, **6**, 4207-4214.
39. C. J. Mable, K. L. Thompson, M. J. Derry, O. O. Mykhaylyk, B. P. Binks and S. P. Armes, *Macromolecules*, 2016, **40**, 7897-7907.
40. N. P. Truong, J. F. Quinn, M. R. Whittaker and T. P. Davis, *Polymer Chemistry*, 2016, **7**, 4295-4312.
41. Q. Tian, C. Fei, H. Yin and Y. Feng, *Progress in Polymer Science*, 2019, **89**, 108-132.
42. B. M. Discher, Y. Y. Won, D. S. Ege, J. C. M. Lee, F. S. Bates, D. E. Discher and D. A. Hammer, *Science*, 1999, **284**, 1143-1146.
43. D. E. Discher and A. Eisenberg, *Science*, 2002, **297**, 967-973.
44. B. Charleux, G. Delaittre, J. Rieger and F. D'Agosto, *Macromolecules*, 2012, **45**, 6753-6765.
45. N. J. Warren and S. P. Armes, *Journal of the American Chemical Society*, 2014, **136**, 10174-10185.
46. M. J. Derry, L. A. Fielding and S. P. Armes, *Progress in Polymer Science*, 2016, **52**, 1-18.
47. S. L. Canning, G. N. Smith and S. P. Armes, *Macromolecules*, 2016, **49**, 1985-2001.
48. J. Chiefari, Y. K. Chong, F. Ercole, J. Krstina, J. Jeffery, T. P. Le, R. T. A. Mayadunne, G. F. Meijs, C. L. Moad, G. Moad, E. Rizzardo and S. H. Thang, *Macromolecules*, 1998, **31**, 5559-5562.
49. S. Perrier, *Macromolecules*, 2017, **50**, 7433-7447.
50. J. Rieger, C. Grazon, B. Charleux, D. Alaimo and C. Jérôme, *Journal of Polymer Science Part A: Polymer Chemistry*, 2009, **47**, 2373-2390.
51. S. Boisse, J. Rieger, K. Belal, A. Di-Cicco, P. Beaunier, M.-H. Li and B. Charleux, *Chemical Communications*, 2010, **46**, 1950-1952.
52. Y. Li and S. P. Armes, *Angew. Chem.-Int. Edit.*, 2010, **49**, 4042-4046.
53. A. Blanazs, J. Madsen, G. Battaglia, A. J. Ryan and S. P. Armes, *Journal of the American Chemical Society*, 2013, **133**, 16581-16587.
54. W.-M. Wan, C.-Y. Hong and C.-Y. Pan, *Chemical Communications*, 2009, 5883-5885.
55. D. Zehm, L. P. D. Ratcliffe and S. P. Armes, *Macromolecules*, 2013, **46**, 128-139.
56. W. J. Zhang, C. Y. Hong and C. Y. Pan, *Macromolecules*, 2014, **47**, 1664-1671.
57. Y. Pei and A. B. Lowe, *Polymer Chemistry*, 2014, **5**, 2342-2351.
58. S. Dong, W. Zhao, F. P. Lucien, S. Perrier and P. B. Zetterlund, *Polymer Chemistry*, 2015, **6**, 2249-2254.
59. M. Semsarilar, N. J. W. Penfold, E. R. Jones and S. P. Armes, *Polymer Chemistry*, 2015, **6**, 1751-1757.
60. L. A. Fielding, M. J. Derry, V. Ladmiraal, J. Rosselgong, A. M. Rodrigues, L. P. D. Ratcliffe, S. Sugihara and S. P. Armes, *Chemical Science*, 2013, **4**, 2081-2087.
61. M. J. Derry, L. A. Fielding and S. P. Armes, *Polymer Chemistry*, 2015, **6**, 3054-3062.
62. A. P. Lopez-Oliva, N. J. Warren, A. Rajkumar, O. O. Mykhaylyk, M. J. Derry, K. E. B. Doncom, M. J. Rymaruk and S. P. Armes, *Macromolecules*, 2015, **48**, 3547-3555.
63. M. J. Derry, L. A. Fielding, N. J. Warren, C. J. Mable, A. J. Smith, O. O. Mykhaylyk and S. P. Armes, *Chemical Science*, 2016, **7**, 5078-5090.
64. Y. Pei, L. Thurairajah, O. R. Sugita and A. B. Lowe, *Macromolecules*, 2015, **48**, 236-244.
65. G. Mellot, J.-M. Guigner, L. Bouteiller, F. Stoffelbach and J. Rieger, *Angewandte Chemie International Edition*, 2019, **58**, 3173-3177.
66. A. Blanazs, A. J. Ryan and S. P. Armes, *Macromolecules*, 2012, **45**, 5099-5107.
67. L. A. Fielding, J. A. Lane, M. J. Derry, O. O. Mykhaylyk and S. P. Armes, *Journal of the American Chemical Society*, 2014, **136**, 5790-5798.
68. Y. Pei, O. R. Sugita, L. Thurairajah and A. B. Lowe, *RSC Advances*, 2015, **5**, 17636-17646.
69. Y. Pei, N. C. Dharsana and A. B. Lowe, *Australian Journal of Chemistry*, 2015, **68**, 939-945.
70. M. J. Rymaruk, S. J. Hunter, C. T. O'Brien, S. L. Brown, C. N. Williams and S. P. Armes, *Macromolecules*, 2019, DOI: 10.1021/acs.macromol.9b00129.
71. S. Y. Khor, N. P. Truong, J. F. Quinn, M. R. Whittaker and T. P. Davis, *ACS Macro Letters*, 2017, **6**, 1013-1019.
72. Y. Pei, A. B. Lowe and P. J. Roth, *Macromolecular Rapid Communications*, 2017, **38**, 1600528.
73. R. Verber, A. Blanazs and S. P. Armes, *Soft Matter*, 2012, **8**, 9915-9922.
74. Y. W. Pei, N. C. Dharsana, J. A. Van Hensbergen, R. P. Burford, P. J. Roth and A. B. Lowe, *Soft Matter*, 2014, **10**, 5787-5796.
75. J. R. Lovett, M. J. Derry, P. Yang, F. L. Hatton, N. J. Warren, Patrick W. Fowler and S. P. Armes, *Chemical Science*, 2018, **9**, 7138-7144.
76. J. H. K. K. Hirschberg, L. Brunsveld, A. Ramzi, J. A. J. M. Vekemans, R. P. Sijbesma and E. W. Meijer, *Nature*, 2000, **407**, 167.
77. N. S. Zaugg, S. Paul Steed and E. M. Woolley, *Thermochimica Acta*, 1972, **3**, 349-354.
78. J. S. Pedersen, *Journal of Applied Crystallography*, 2000, **33**, 637-640.



ARTICLE

Journal Name

79. A. Winkler and P. Hess, *Journal of the American Chemical Society*, 1994, **116**, 9233-9240.
80. O. Glatter and O. Kratky, *Small-angle X-ray scattering*, Academic Press: London, 1982.
81. A. P. Chatterjee, *Journal of Chemical Physics*, 2010, **132**, 224905.
82. H. Rehage and H. Hoffmann, *The Journal of Physical Chemistry*, 1988, **92**, 4712-4719.
83. N. A. Spenley, M. E. Cates and T. C. B. McLeish, *Physical Review Letters*, 1993, **71**, 939-942.
84. C. A. Dreiss, *Soft Matter*, 2007, **3**, 956-970.
85. S. J. Suresh and V. M. Naik, *The Journal of Chemical Physics*, 2000, **113**, 9727-9732.
86. G. Allen and E. F. Caldin, *Transactions of the Faraday Society*, 1953, **49**, 895-905.
87. D. H. Williams and I. Fleming, *Spectroscopic Methods in Organic Chemistry*, McGraw-Hill, 2008.

View Article Online
DOI: 10.1039/D1SC03156B

